

ARTICLE INFO

Received : May 28, 2020

Revised : July 27, 2020

Accepted : October 05, 2020

CT&F - Ciencia, Tecnología y Futuro Vol 10, Num 2 December 2020, pages 73 - 83

DOI : <https://doi.org/10.29047/01225383.258>



ctyf@ecopetrol.com.co

HEAVY OIL AND HIGH-TEMPERATURE POLYMER EOR APPLICATIONS

■ APLICACIONES EOR DE INYECCIÓN DE POLÍMERO EN YACIMIENTOS DE CRUDO PESADO Y ALTA TEMPERATURA

Ruben-Hernán, Castro-García^{a*}; Sebastián, Llanos-Gallo^b; Jenny-Liseth, Rodríguez-Ardila^b; Hendersón-Ivan, Quintero-Perez^a; José-Francisco, Zapata^c; Eduardo, Manrique^a.

ABSTRACT

Polymer flooding represents the most common chemical enhanced oil recovery (CEOR) method used at commercial scale. In this process, the polymeric solutions (generally hydrolyzed polyacrylamide - HPAM) are injected to improve the oil/water mobility ratio (M). However, due to mechanical, chemical, bio, and thermal degradation, polymer viscosity losses can occur, causing a negative impact on oil sweep efficiency. In this case, biopolymers seem to be promising candidates in EOR applications with special structural characteristics, which result in excellent stability in harsh environments with high temperatures, ionic forces, and shear stresses. This paper presents the laboratory evaluation of Scleroglucan (SG) and a commercial sulfonated polyacrylamide (ATBS) in synthetic brine, representative of a Colombian heavy-oil field. The effects of ionic strength, pH, temperature, and shear degradation effects on polymer viscosity were also evaluated. For SG, the results reflect its tolerance to high salinities (0-5%wt), ionic strengths (Na⁺, K⁺, Ca²⁺, and Mg²⁺), shear rates (0-275,000 s⁻¹), temperatures (30, 50, 80 and 100 °C), and pH variations (3-10). The biopolymer was capable of preserving its viscous properties and stability after the effect of these variables. Finally, the target viscosity (set as 17 cp) was achieved with a lower concentration (2.7 times) than the ATBS polymer tested.

RESUMEN

La inyección de polímeros representa la recuperación mejorada química de petróleo (CEOR, de sus siglas en inglés) más común utilizada a escala comercial. En este proceso, las soluciones poliméricas (generalmente poliacrilamida hidrolizada - HPAM) se inyectan para mejorar la relación de movilidad aceite/agua (M). Sin embargo, debido a las degradaciones mecánicas, químicas, biológicas y térmicas, pueden producirse pérdidas de viscosidad del polímero, lo que afecta negativamente la eficiencia de barrido de aceite. En este caso, los biopolímeros surgen como candidatos prometedores en aplicaciones EOR que tienen características estructurales especiales que les permiten exhibir una excelente estabilidad en ambientes hostiles con altas temperaturas, fuerzas iónicas y esfuerzos de corte. Este trabajo presenta la evaluación de laboratorio de Escleroglucano (SG) y una poliacrilamida sulfonada comercial (ATBS) en salmuera sintética representativa de un campo de petróleo pesado colombiano. También se evaluaron los efectos de la fuerza iónica, el pH, la temperatura y los efectos de degradación por esfuerzo de corte sobre la viscosidad del polímero. Para SG, los resultados reflejan su tolerancia a altas salinidades (0-5% en peso), fuerzas iónicas (Na⁺, K⁺, Ca²⁺ y Mg²⁺), velocidades de corte (0-275,000 s⁻¹), temperaturas (30, 50, 80 y 10 °C) y variaciones de pH (3-10). El biopolímero fue capaz de preservar sus propiedades viscosas y estabilidad después de la afectación de estas variables. Finalmente, la viscosidad objetivo (establecida en 17 cP) se logró con una concentración más baja (2.7 veces) en comparación con el polímero ATBS evaluado.

KEYWORDS / PALABRAS CLAVE

Enhanced oil recovery (EOR) | Biopolymer | Scleroglucan | Sulfonated polyacrylamide | ATBS | Filter ratio | Shear degradation. Recuperación mejorada de petróleo (EOR) | Biopolímero | Escleroglucano | Poliacrilamida sulfonada | Relación de filtrabilidad | Degradación mecánica.

AFFILIATION

^aEcopetrol S.A. - Instituto Colombiano del Petróleo (ICP), Vía Piedecuesta Km.7, Piedecuesta, Santander-Colombia.
^bUniversidad Industrial de Santander (UIS), Carrera 27 Calle 9, Bucaramanga, Colombia.
^cEcopetrol S.A. Cra. 13 N° 36-24, Bogotá, Colombia
*email: rubenhe.castro@ecopetrol.com.co

1. INTRODUCTION

Most oil fields have an accelerated rate of production and depletion of reserves due to high demand and a low global supply of hydrocarbons. This situation demands developing and improving conventional EOR techniques with tolerance to adverse high temperature and salinity (HTHS) conditions [1]-[3]. For decades, injection of water-soluble synthetic polymers, generally polyacrylamides [4], is the more frequent flooding technique used worldwide to improve oil efficiency sweeping and oil/water mobility control in the reservoir with oil recovery percentages between 5-30% [5]-[7]. However, synthetic polymers, specifically partially hydrolyzed polyacrylamides (HPAM), have several disadvantages that limit their application in HTHS reservoirs. The use of conventional HPAM is not feasible at temperatures higher than 120°C, brines with organic traces, and total dissolved solids (TDS) greater than 5%w/w, high shear rates ($> 5,000 \text{ s}^{-1}$), and low tolerance to oxide-reduction conditions [8]-[10]. On the other hand, from an environmental point of view, synthetic polymers injection in EOR applications involves significant amounts of raw material (i.e., acrylates) that result undesirable in an eco-friendly scenario. Hence, the industry's efforts are currently focused on the research, development, evaluation, and application of highly tolerant and stable polymers, mechanically, thermally, and chemically, with a green impact at field-scale [11],[12].

The study and application of polysaccharides for EOR applications in HTHS reservoirs are gaining interest in the oil industry. Some of the most studied products include:

- Xanthan and diutan gums,
- Hydroxyethylcellulose (HEC) and carboxymethylcellulose (CMC),
- Schizophyllan and Scleroglucan.

A recent study suggests that these chemicals are considered promising in polymer flooding EOR processes, as replacement of HPAM polymers. The latter is based on the fact that biopolymers show high tolerance to mechanical degradation and high viscosities at lower concentrations as compared with conventional polymers [13].

Xanthan gum has been widely used in EOR processes as it exhibits high resistance to electrolytes and is mechanically stable at high shear stresses at temperatures below 90°C. Low purity, injectivity, and high bacterial degradation are among other limitations [14]. It is worth noting that diutan gum and Schizophyllan can tolerate HTHS conditions (up to 150 °C) due to its higher pseudo-plasticity and mechanical stability [15].

Recently, Schizophyllan, a neutral polysaccharide obtained in liquid form, was first tested at field conditions ($T > 135 \text{ }^\circ\text{C}$, TDS of

186 g/L, and 60 ppm Fe^{+2}) in Germany [16],[17]. This biopolymer showed good mechanical stability at high shear stresses ($35,000 \text{ s}^{-1}$). The injectivity of a 350 ppm solution was stable (200-2,000 mD formation) with steady resistance factors (RF) throughout the test. Schizophyllan also showed better rheological performance compared to xanthan gum and polyacrylamides. Additionally, as a lesson learned, they required nitrogen blanketing due to the transport and preparation of the biopolymer before injection (the oxygen-free environment must be 100% secured). Finally, the injection of this biopolymer showed a 25% increase in oil recovery as compared to water injection. The authors reported that the proximity between the injector and the producing wells is a good indication of the effect of the biopolymer for the assessed period (6-7 months), followed by rigorous monitoring and sampling throughout execution of the pilot [17]. However, the standard selection criteria of biopolymers (i.e., solubility, injectivity, adsorption, etc.) is not well documented in the literature.

The application of Scleroglucan as an active agent in EOR processes emerges as an environmentally friendly alternative for harsh conditions in reservoirs with high salinity, temperature, and shear stresses, due to its rigid, triple helix structure [12],[18]. Several authors have reported the excellent performance of Scleroglucan in adverse reservoir conditions [19],[20], stability, and high retention for three months at 80°C in high salinity [21]-[23]. Scleroglucan shows great potential with better performance as compared to xanthan gum and polyacrylamides in terms of thermal, chemical and mechanical stability, and oil recovery [12]. Recently, Scleroglucan was evaluated at a laboratory scale for the Adena field reservoir conditions, Colorado, United States. Stability tests were run for temperatures up to 115°C and 180 days, shear rates of $175,000 \text{ s}^{-1}$ and Fe^{2+} and H_2S content of 500 ppm and 200 ppm, respectively. Adena field reservoir temperature is 82°C, and the average rock properties are 19.7% porosity (\emptyset) and permeability (K) of 805 mD. Main fluid properties are crude oil gravity of 42°API and brine of 8,000 TDS (Total Dissolved Solids), and 35 ppm TSS (Total Suspended Solids) [19],[20]. The concentration determined for these conditions was 300 ppm of the biopolymer to achieve the target viscosity of 1.4 cP. The static evaluation results reflect that the Scleroglucan showed filtering capacity similar to that of water, and stability after 90 days at 82°C without adverse effects on viscosity. Based on the foregoing, this study compares the performance of Scleroglucan (SG) and a commercial sulfonated polyacrylamide (ATBS), based on a laboratory evaluation at static conditions in controlled systems. The purpose of this study is to identify the best polymer candidate for a specific case of a Colombian heavy oilfield (100°C and 3,800 ppm TDS) in terms of stability by thermal (50°C and 100°C up to 180 days), chemical (different ionic conditions) and mechanical (up to $275,000 \text{ s}^{-1}$) effects.

2. EXPERIMENTAL DEVELOPMENT

MATERIALS

A commercial Scleroglucan (SG) of molecular weight (MW) $\approx 4\text{-}5$ MMDa and a sulfonated polyacrylamide (ATBS-25%) with MW ≈ 13 MMDa, were used in this experimental study. For the preparation

of the synthetic brine, 2.9674 g/L NaCl, 0.13 g/L KCl, 0.239 g/L $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$, and 0.583 g/L $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$ in type II water (pH=6) were used.

METHODS

THERMOGRAVIMETRIC ANALYSIS (TGA)

The mass conversion of polymers in an inert atmosphere was determined using a Q50 thermogravimetric analyzer (TA Instruments, Inc., New Castle, DE) under N₂ flow at 100 mL/min with an optimizing heating rate where sequence programming is started at 30°C with 5°C/min up to 800°C. The procedure consists in weighing a specific amount in the sample holder due to diffusion effects. The Q Series- Q500-TGA commercial software is used to export the analysis data.

PREPARATION OF POLYMER SOLUTIONS

Synthetic polymer solutions at a fixed concentration of 2,500 mg/L were prepared according to API-RP-63 [24]. SG solutions were prepared following the practices recommended by the supplier [20], considering agitation, total solubility time, and hydration to ensure homogeneity, stability, and avoid possible negative effects [25]. First, stir the synthetic brine with a propeller-type agitator at speed enough to generate a vortex of 1/3 of total volume, then sprinkle the biopolymer in the vortex shoulder continuously. Second, stir the mixture at 800 rpm for 10 minutes and heat the solution until it reaches 40 °C. Third, stir the biopolymer solution in an immersion blender (ultra-turrax) at 20,000 rpm for 5 minutes. Lastly, observation analysis, turbidity, and transmittance measurements are required for quality control of a biopolymer solution.

RHEOLOGICAL TESTS

Rheological measurements for polymer solutions were performed using a rheometer Anton Paar MCR 702 (Anton Paar GmbH, AUT) with the concentric cylinder's geometry, equipped with a Peltier temperature device and pressure cell in a nitrogen atmosphere. Each measurement was performed in a range of shear rates of 4-400 s⁻¹, temperatures of 80-100°C, and pressure of 530 psi. For analysis and treatment of rheometer data, a RheoCompass software was used. A DV2T Viscosimeter (Brookfield Ametek, USA) was used for static measurements at a constant shear rate (7.3 s⁻¹) using UL and DIN adapter spindles following standard practices [24].

HYDRODYNAMIC MOLECULE SIZE

The hydrodynamic molecule size was obtained by dynamic light scattering (DLS) measurements using a Zetasizer ZS (Malvern Panalytical, UK) after agitation for 15 min at 30°C and 60°C. Polymer solutions were prepared in synthetic brine of NaCl (0, 0.01, 0.1, 1, and 10%w/w) to determine the salt concentration effect. Parameters such as viscosity, refractive index (1.3335-1.3366), absorbance (0.02-0.06), and wavelength (195 and 285 nm) were measured for each sample.

CHEMICAL STABILITY: ELECTROLYTES EFFECT

The cationic effects of Na⁺, Ca²⁺, and Mg²⁺ were evaluated for both polymers in aqueous chloride salts. Viscosity measurements were carried out in a viscosimeter at 7.3 s⁻¹ and temperatures of 30, 50, 80 y 100°C. Viscosities at temperatures above 60°C were tested in the rheometer.

THERMOCHEMICAL STABILITY

The polymer solutions were assessed at different temperatures (30°C to 100°C), as described in the rheology test. Also, polymer solutions in the presence of Fe²⁺ (0 and 3 ppm) were exposed to high temperature (105°C) for six months. Each sample is prepared and embased in airtight bottles in a vacuum chamber, and then, the bottles are exposed at 105°C for 180 days in a heating oven. Last, viscosity measurements for each container are monitored every 30 days at 7.3 s⁻¹ in an inert atmosphere (0 ppm O₂).

FILTERABILITY TEST

Tests of Filterability ("filter") ratio (FR) and cumulative filterability of polymer solutions were carried out according to the API-RP-63 method [24]. For the FR, nitrocellulose membrane filters of 1.2 μm and 5 μm (Merck KGaA, Germany) were used. The accumulated filtration time was recorded for every 100 mL of filtrate until 300 mL, at a constant pressure of 30 psi. For the cumulative filterability test, a 5 μm filter was used, recording the accumulated filtration pressure for 500 mL at a continuous rate of 2 mL/min and 30°C.

MECHANICAL STABILITY

Mechanical degradation tests of the polymer solutions were carried out following the technical test instructions of API RP63 [24] recommended practices. This procedure is performed to simulate the flow conditions of the polymer solutions through the surface facilities and the mechanical well state. In this test, the shear rate evaluated ranged between 5,000 and 275,000 s⁻¹. Mechanical degradation is carried out flowing the pressurized polymer solution through a capillary tube at different flow rates obtained for each pressure recording time and weight of the sheared fluid. Each viscosity of the sheared solution is measured at 7.3 s⁻¹ and room temperature. The shear rate ($\dot{\gamma}$) of the polymer solution is calculated based on the flow rates (Q) and the internal radius of the capillary (R) according to Equation 1:

$$\dot{\gamma} = \frac{4Q}{\pi R^3} \quad (1)$$

MODELING

RHEOLOGICAL BEHAVIOR

The Carreau-Yasuda model [26] includes rheological parameters for non-newtonian fluids such as relaxation time (λ), related to the time for the polymer system to return to equilibrium in response to a disturbance. Intrinsic parameters, n and α are related to the transition behavior, and the viscosity parameters (η_0 and η_∞) indicate the fluid behavior at zero and infinite shear rate. The Carreau-Yasuda model is expressed as follows [26],[27]:

$$\eta = \eta_\infty + (\eta_0 - \eta_\infty) \left[1 + (\lambda\dot{\gamma})^\alpha \right]^{(n-1)/\alpha} \quad (2)$$

Where η (cP) and $\dot{\gamma}$ (s⁻¹) are the viscosity and shear rates, respectively. The root-mean-square error (RSME%) was used to estimate the proper fit of the model used.

3. RESULTS

THERMAL CHARACTERIZATION

The weight loss (%) and its conversion as a function of temperature for both solid polymers at inert atmosphere are shown in **Figure 1**. The behavior of both materials corresponds to a mass loss proportional to the increase in system temperature. **Figure 1a** shows the thermogram for the Scleroglucan. The most significant mass reduction of the material was observed in temperature ranges of <100 °C, 250-350 °C and 450-500 °C, respectively. Each of these weight losses corresponds to the loss of surface-adsorbed

water, CO_2 from carboxyl groups (COO^-) decomposition [28], depolymerization reaction [29], and the volatile products of lower molecular weight [30]. **Figure 1b** presents the TGA results for the sulfonated polyacrylamide. In this case, four regions with high mass conversion were registered in temperature ranges of $<100^\circ\text{C}$, $350\text{--}380^\circ\text{C}$, $400\text{--}450^\circ\text{C}$, and $550\text{--}650^\circ\text{C}$, respectively. These mass reductions are attributed to the breaking of the copolymer bonds that gives rise to the release of water ($\leq 100^\circ\text{C}$), loss of structural water by dehydroxylation ($\leq 200^\circ\text{C}$), and loss of NH_3 , SO_2 , CO , and CO_2 groups [31, 32]. In both cases, the mass loss at 600°C indicates significant percentages of total degradation (up to 100%). However, the higher thermal stability of the sulfonated polyacrylamide can be attributed to structural and chemical differences (i.e. presence of functional groups $-\text{COO}^-$, $-\text{CH}_2-\text{SO}_3^-$, CONH_2 , etc.) compared to SG [31]. Further, the percentage of moisture for the scleroglucan and the sulfonated polyacrylamide at 100°C in an inert atmosphere correspond to 11% and 9%, respectively [12].

RHEOLOGICAL BEHAVIOR OF POLYMERIC SOLUTIONS

Figure 2, presents the viscosity behavior of SG and sulfonated polyacrylamide as a function of the shear rate. These tests were run for different polymer concentrations prepared in synthetic brine (TDS 3,800 ppm) at 100°C in a pressurized nitrogen system. The viscous behavior of both polymers tends to increase proportionally with the concentration. Nonetheless, SG exhibits similar viscosities at lower concentrations as compared to the sulfonated polymer due to its configuration and structure. Both polymer solutions show a non-Newtonian behavior. The rheological behavior of both polymer solutions has a shear thinning type due to viscosity reduction with the shear rate increase. However, SG exhibits higher viscosity than the sulfonated polyacrylamide due to its rod-like structure compared to the branched configuration of the ATBS polymer. Additionally, the thermal resistance of the biopolymer generates

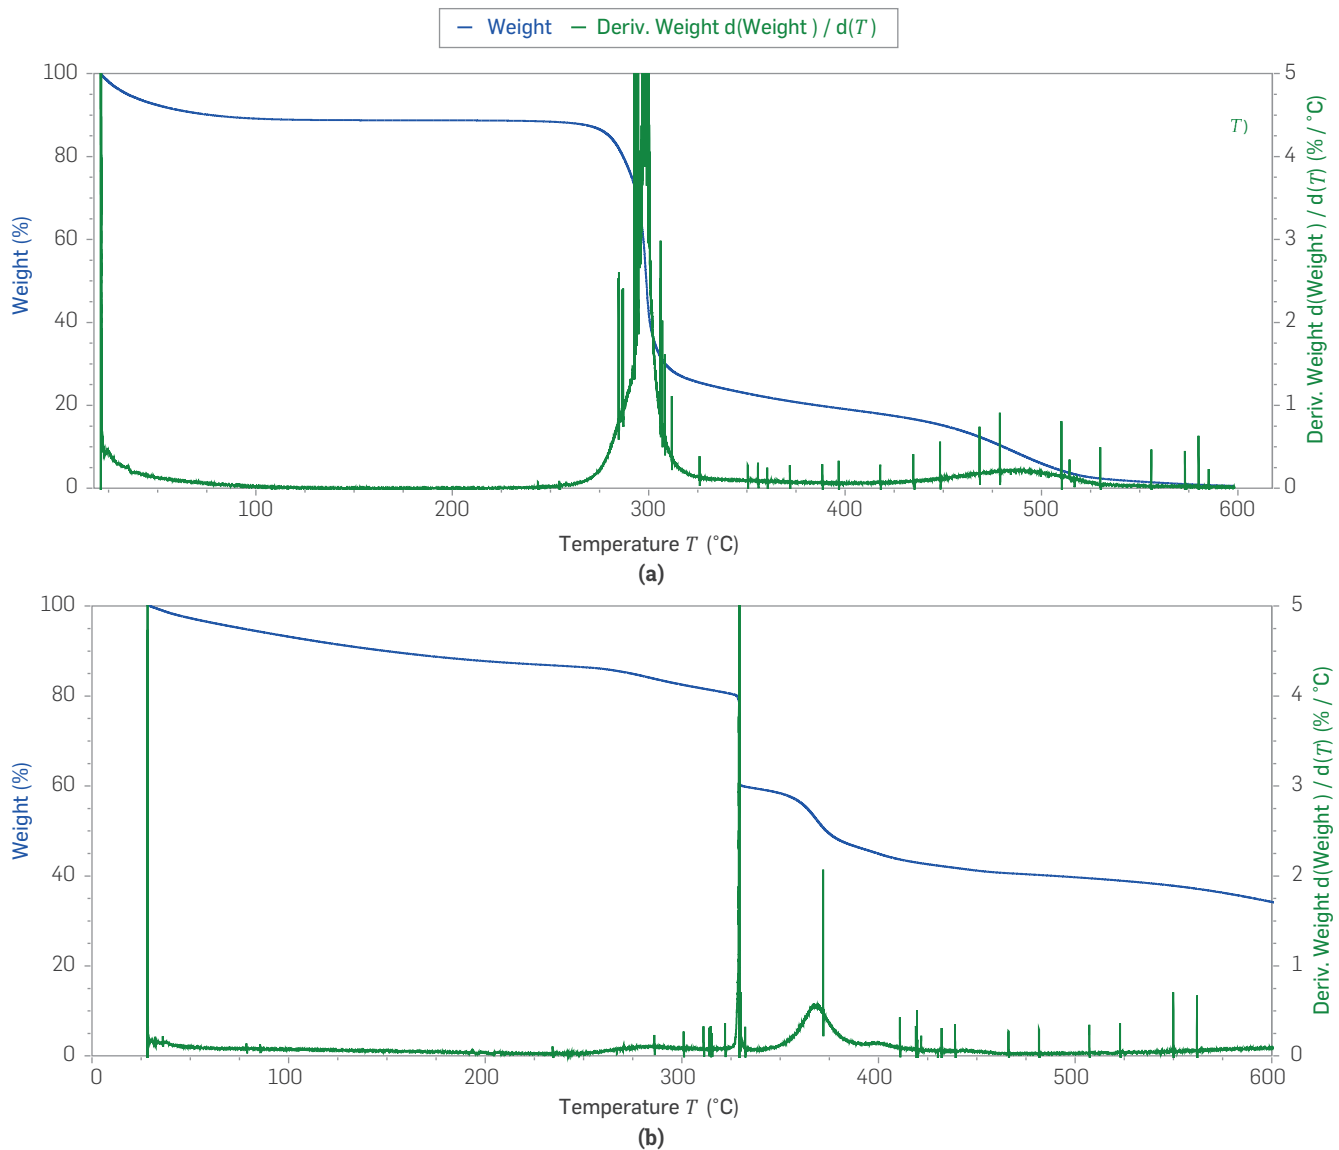


Figure 1. Thermograms of (a) Scleroglucan (SG) and (b) sulfonated polyacrylamide (ATBS) in an inert atmosphere from 30°C to 600°C .

higher stability by the retention of water molecules in their dense structure [12]. These properties represent an optimum scenario for polymer injection. Specifically, the SG polymer solution shows better viscosity performance reducing the concentration up to 3 times to obtain the same target injection viscosity (17 cP) vis-à-vis sulfonated polyacrylamide.

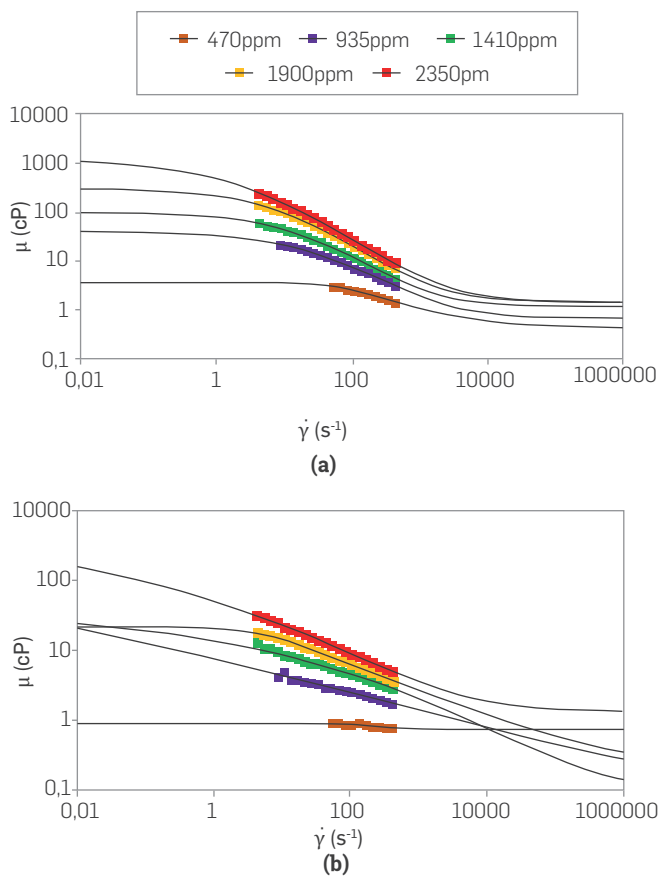


Figure 2. Rheological behavior of (a) scleroglucan, and (b) sulfonated polyacrylamide solutions for different polymer concentrations prepared in synthetic brine (TDS 3,800 ppm) at 100 °C.

The Carreau-Yasuda model parameters for the rheological behavior of polymer solutions are shown in **Table 1**. SG viscosity parameters at zero and infinity times (η_0 and η_∞) are higher than the sulfonated polyacrylamide solutions. The relaxation times (λ) are higher for Scleroglucan due to its low viscoelasticity compared to

polyacrylamide [33]. For both polymer solutions, there are three regions with pseudo-plasticity indices (n) less than one (1), common from a shear-thinning fluid [34], where a first region or first plateau corresponding to viscosity at low shear rates are higher for all SG concentrations. The second region or pseudo-plasticity zone is similar for both polymers. Nonetheless, the ATBS is slightly better due to the higher viscoelasticity behavior of branched polymer chains in comparison with the rod-like structure of scleroglucan [35].

The last region (second plateau), corresponding to high shear conditions, shows higher viscosities for SG polymer due to low mechanical and thermal degradation effects. However, the final viscosity in both cases is similar to water viscosity. However, scleroglucan viscosities are higher than 1 cP at the infinity shear rate due to neutral nature and rod-like structure after the shear effect.

In this case, 17 cP at 100 °C it was determined as target viscosity considering the oil/water mobility ratio close to 1. For SG, the target viscosity of 17 cP reached with the 2,500 ppm of the ATBS polymer is achieved with 935 ppm at the same temperature and salinity conditions. **Figure 3** shows the polymer viscosities as a function of polymer concentration in synthetic brine (TDS 3,800 ppm) at 100 °C. It should be noticed that the SG viscosification potential in high-temperature conditions is significant at the polymer concentration increases. Therefore, the polymer concentration of SG and sulfonated polyacrylamide compared in the different static evaluations is 935 ppm and 2,500 ppm, respectively.

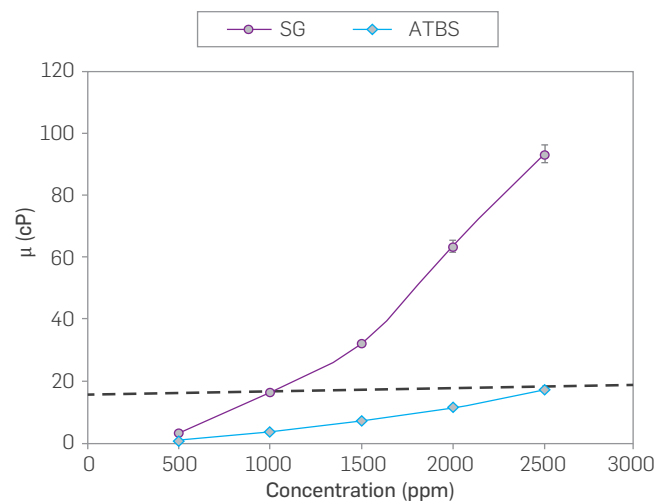


Figure 3. Polymer viscosity as a function of polymer concentrations (0.05-0.25%wt) in synthetic brine (3,800 ppm TDS) at 20 s⁻¹, and 100 °C.

Table 1. Carreau-Yasuda model parameters for the rheological behavior of scleroglucan (SG) and sulfonated polyacrylamide (ATBS) solutions at different polymer concentrations in synthetic brine (3,800 ppm TDS) at 100 °C.

Parameter	SG					ATBS				
	Concentration (ppm)									
	470	935	1410	1900	2350	500	1000	1500	2000	2500
η_0	3.5302	41.730	97.067	305.920	1,253.20	0.886	1.777	21.822	39.158	542.090
η_∞	0.4187	0.6869	1.1918	1.4287	1.5296	0.017	0.100	0.110	0.186	1.312
λ	0.0152	0.0245	0.0648	0.1758	0.3739	0.001	0.010	0.011	0.099	0.228
α	1.6744	0.5389	0.6653	0.7149	0.4838	0.111	0.139	0.182	1.269	1.161
n	0.4161	0.0001	0.0342	0.0840	0.0228	0.051	0.143	0.443	0.601	0.961

THERMOCHEMICAL STABILITY

Scleroglucan and sulfonated polyacrylamide solutions were assessed at different temperatures (30 °C to 100 °C), as shown in **Figure 4**. The viscosity behavior of SG outperforms the sulfonated polyacrylamide system within the range polymer concentration (470 to 2,500 ppm), and temperatures (30° to 100 °C) are evaluated. The ATBS polymer studied shows a lower viscous range (25.8 cP at 100 °C) with a higher polymer concentration (2,500 ppm).

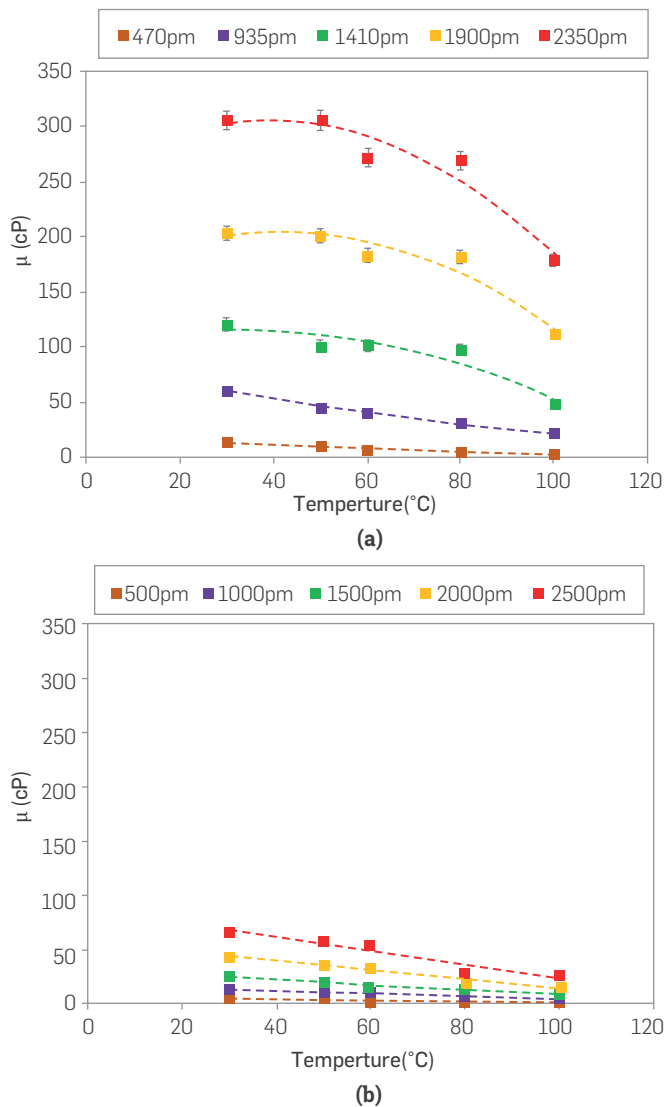


Figure 4. Viscosity behavior of (a) SG and (b) ATBS polymers at different concentrations (470-2,500 ppm) in synthetic brine (TDS 3,800 ppm) and temperatures (30° to 100 °C) at 7.3 s⁻¹.

The thermochemical stability of polymer solution represents a critical criterion for polymer selection in polymer flooding. Harsh reservoir conditions can negatively impact polymer viscosity due to intermolecular forces and polymer chain interactions, decreasing it due to electrolytes and high-temperature effects [35],[36]. The SG and ATBS polymer solutions were also evaluated over time (0 to 180 days) at 105 °C with polymer concentration (935 ppm and

2,500 ppm) to reach the target viscosity of 17 cP in the presence of Fe²⁺ in an inert atmosphere. SG showed a steady viscosity behavior during 180 days with losses below 1 % from the initial viscosity. The ATBS polymer lost less than 20 % of its initial viscosity after 90 days, with only the temperature effect under anoxic conditions, as reported in the literature [37]. The behavior of SG solutions (935 ppm) and sulfonated polyacrylamide (2,500 ppm) under different pH range at different temperatures are shown in **Figure 5**. The chemical nature of each system plays a fundamental role in their viscosity behavior, depending on the solution pH. In the case of scleroglucan, which has a neutral character, the viscosity is not adversely affected when the system is hugely acidic (pH=2) or moderately basic (pH=10). However, there is evidence when the pH is higher than 13, the viscosity is drastically reduced due to the denaturation of the triple helix structure with high alkali concentrations [38],[39]. The ATBS polymer, which is a polyelectrolyte, is affected by the pH variation, which makes it dependent on the electrical charges, and its stability decreases when it is an acidic system.

The polymer solution system was also assessed under different ionic

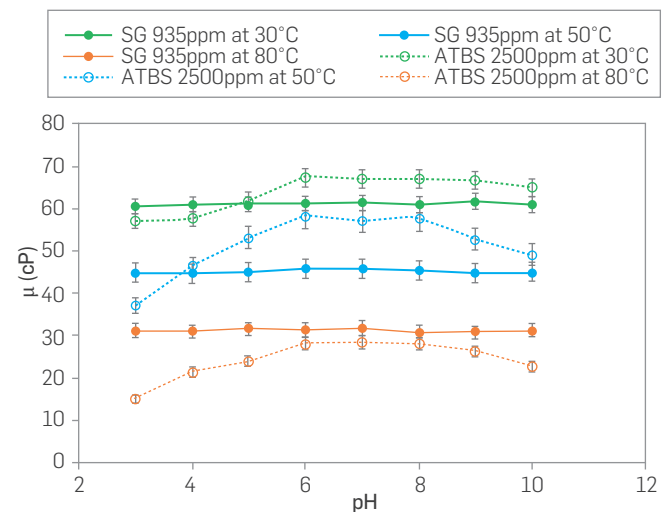


Figure 5. Viscosity behavior of SG (935 ppm) and ATBS polymer (2,500 ppm) as a function of pH at different temperatures (30° to 80 °C) in synthetic brine (TDS 3,800 ppm) and 7.3 s⁻¹.

strength (0.043, 0.086, 0.171, and 0.342) with the concentration of monovalent and divalent ions (Na⁺, Ca²⁺, and Mg²⁺) present in the formation water to observe the solubility, hydration, and viscosity depending on the reservoir temperature. The viscosity of both polymer solutions as a function of NaCl concentrations (0 to 5 %w/w NaCl) is shown in **Figure 6**. A similar trend is evident in both polymers after 0.15 %w/w. Scleroglucan exhibits higher stability, from 0 to 5 %w/w of NaCl, which confirms its high tolerance to high salinity and temperature, as reported in the literature [25],[40].

Figures 7 and 8 show the effects of divalent cations (Ca²⁺ and Mg²⁺) on SG and ATBS polymer viscosities. **Figure 7**, shows the viscosity behavior of both polymer systems in the presence of different concentrations of CaCl₂. The scleroglucan viscosity is stable, with the calcium concentration increasing in the solution for all temperatures evaluated. Conversely, the sulfonated polyacrylamide solution showed an apparent decrease in viscosity, increasing calcium concentration and temperatures. This case confirms the higher sensitivity of polyacrylamide by divalent ions due to the reduction of polymer chain entanglement [41].

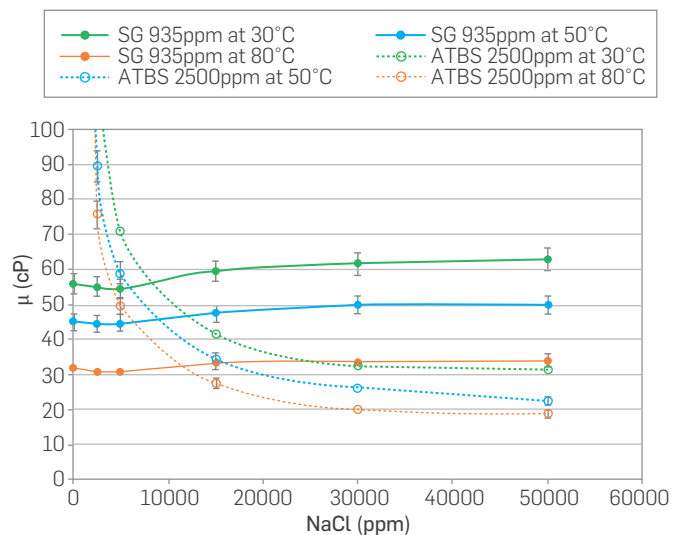


Figure 6. Viscosity behavior of SG (935 ppm) and sulfonated polyacrylamide (2,500 ppm) at different temperatures (30° to 80 °C) and NaCl concentrations (0 to 50,000 ppm) at 7.3 s⁻¹.

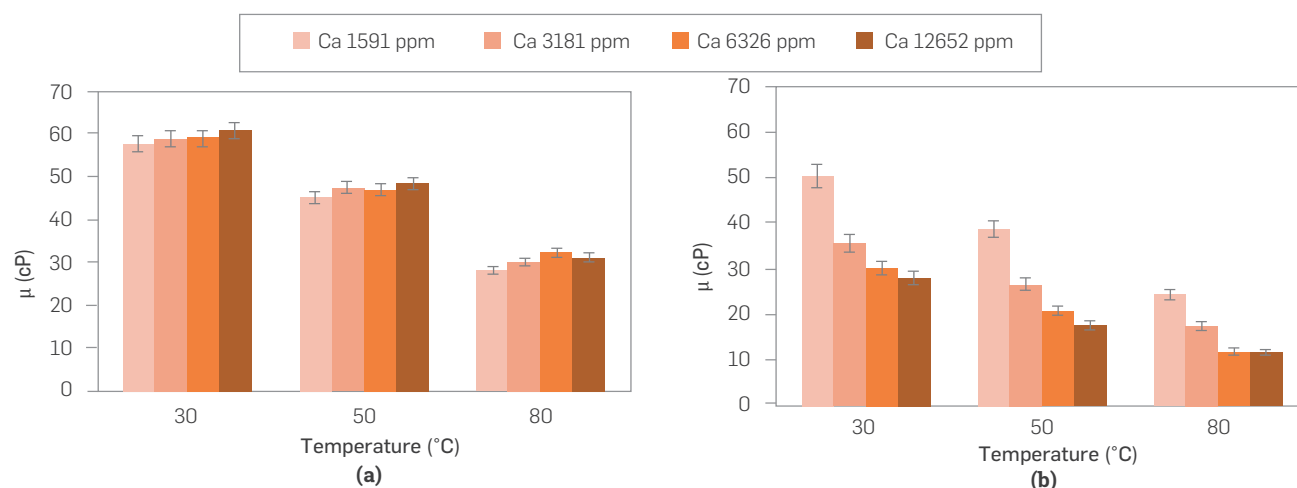


Figure 7. Viscosity behavior of (a) scleroglucan (935 ppm) and (b) sulfonated polyacrylamide (2,500 ppm) in synthetic brine with different ionic strength of Ca²⁺ at temperatures of 30°, 50° and 80°C and 7.31 s⁻¹.

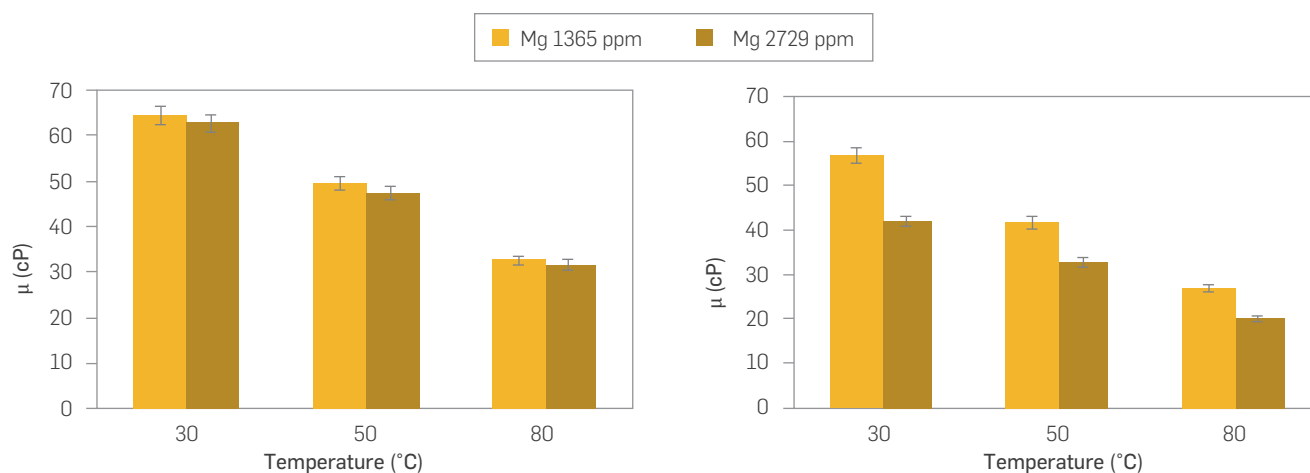


Figure 8. Viscosity behavior of (a) scleroglucan (935 ppm) and (b) sulfonated polyacrylamide (2,500 ppm) in synthetic brine with different ionic strength of Mg²⁺ at temperatures of 30°, 50°, and 80°C and 7.31 s⁻¹.

The behavior of the polymer solutions in the presence of Mg²⁺ ion shows a viscosity reduction effect in both polymers. Although both polymer viscosities decrease with the increase of Mg²⁺ concentration, SG seems to be more tolerant than the ATBS polymer at the conditions assessed (Figure 8). The impact on the viscosity reduction is the result of the divalent ion interaction with the amine groups present in the branched-chain of the sulfonated polymer [31].

HYDRODYNAMIC SIZE BEHAVIOR

Scleroglucan and sulfonated polyacrylamide configurations in the aqueous phase are detected as spherical shape by the DLS technique, as shown in Figure 9. In this case, it is considered that SG and ATBS polymer molecules can be circular or linear organization [42],[43], depending on the interaction between molecules when increasing the concentration, temperature, salinity, pH, and other. This structural behavior determines the polymer viscosity in solution; however, the accuracy of the DLS technique for this type of macromolecules is limited by laser angles, absorbance, refractive index, dielectric constant, and viscosity [43]. In this study, DLS measurements were used to relate the behavior of polymers hydrodynamic size and its viscosity with the variation of NaCl concentrations.

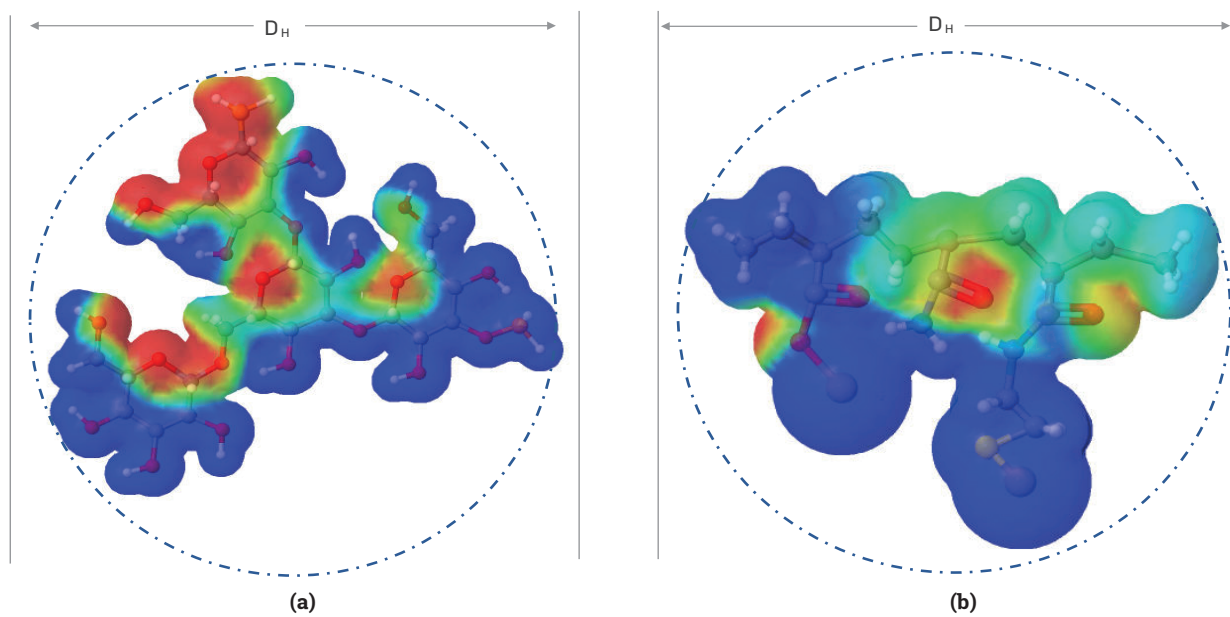


Figure 9. Hypothetical electrostatic potential and hydrodynamic shape of a structural unit of a) scleroglucan (SG) and b) sulfonated polyacrylamide (ATBS) in aqueous phase. The red color indicates regions of high electron density, blue regions represents low electron density, and yellow and green represent a homogeneous electron balance.

The hydrodynamic behavior of polymer solutions shows high stability when salinity is less than 1 % of NaCl. Nonetheless, after the aggregates, the entanglement reduces the average size of sulfonated polyacrylamide, where this effect is directly proportional to the viscosity system, reducing it more than 50 % in both temperatures evaluated. Both polymers have similar viscosity and different aggregates size within 1 % and 10 %wt of NaCl. The sulfonated polymer coils up at high NaCl concentration reducing the hydrodynamic size and interaction of the polymer chains, causing a reduction in the viscosity [44].

Regarding SG, the viscosity and hydrodynamic behavior are less significant with the electrolyte charge and temperature effects, where viscosity reduction is less than 20 % (Figure 10). Both

polymers are governed mainly by factors such as electrostatic interactions [45], Van der Waals forces [46][47], hydrogen bonding [48],[49], hydrophobic interactions [50], and excluded volume effects [51] that govern the hydrodynamic behavior of the aqueous configuration. Hydrogen bonds could be the primary interaction in the stabilizing intra-molecular shape or formation of junction zones for scleroglucan due to helices and β -sheets in its structure [52].

As regards ATBS, the electrostatic interactions and hydrogen bonds being are the main dominant effects due to the anionic nature and the intermolecular entanglement [36]. This hydrodynamic size (DH) behavior of a polymer solution is a crucial parameter for the understanding of flow resistance or size distribution limits of polymer in terms of flow in the porous medium [5].

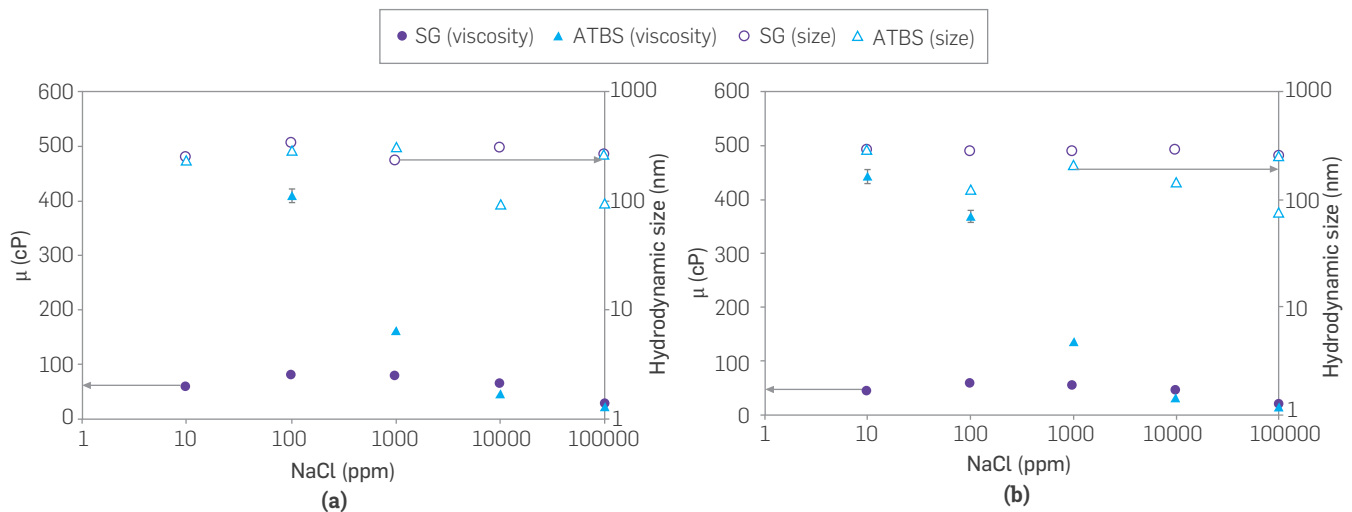


Figure 10. Effect of NaCl concentrations (0-10 %wt) on the hydrodynamic size and viscosity behavior of SG and ATBS polymers at a) 30 °C and b) 60 °C and atmospheric conditions.

MECHANICAL STABILITY

Figure 11a shows the flow time of polymer solutions through a pore-size nitrocellulose membrane of 1.2 and 5 μm , which restrict the flow when the system is pressurized. Both polymer solutions have a filterability ratio between 1 and 1.2, regardless of the time in which the same volume is filtered [24]. SG solutions flow through the filter in less than 1 minute regardless of the membrane pore size and despite the rigid rod-like structure of this biopolymer. On the contrary, the ATBS polymer solutions required 100 minutes to filter the same volume. The structure of this sulfonated polymer corresponds to a set of aggregates that tend to pass through the pore with greater difficulty. This behavior is related to Figure 11b, where the same volume is filtered at a constant flow rate (2 mL/min) in a pore size of 5 μm . In this system, the solution with Scleroglucan has a lower energy expenditure in terms of pressure to be injected compared to sulfonated polyacrylamide in a significant proportion. The aggregate sizes of the sulfonated polyacrylamide (DH <5 μm) tend to trap the space by mechanical effects to the point where the system continually flows at a specific pressure (120 psi). Conversely, SG exhibits a steadier behavior, showing a maximum flow pressure

of 14 psi after the 80 pore volume is injected (PVI). However, it is still much lower than that required by the synthetic polymer. Its behavior is perhaps attributable to the rearrangement of the dense rod-structure passing through a linear space.

For the mechanical degradation of the polymer solutions, each system was evaluated at different shear rates to determine the viscosity losses associated with mechanical degradation. Figure 12 shows the viscosity loss of Scleroglucan and sulfonated polyacrylamide as a function of the shear rate. In this scenario, the viscosity losses of the SG are less than 30% at shear rates of up to 275,000 s^{-1} . These results confirm the low mechanical degradation results reported in the literature with much lower shear rates (up to 1,000 s^{-1}) [20]. However, viscosity losses of the sulfonated polyacrylamide reach up to 80% of its initial viscosity under the same conditions, which lead to a technical-operational disadvantage. The injection of SG would allow the current operation of conventional waterflooding, the use of flow regulating valves, selective strings, and well spacing without any significant adverse effect on the polymer viscosity as presented in the mechanical stability test when subjected to high cutting rates. Conversely, this advantage over synthetic polymer implies lower resources and equipment in the application of field technology.

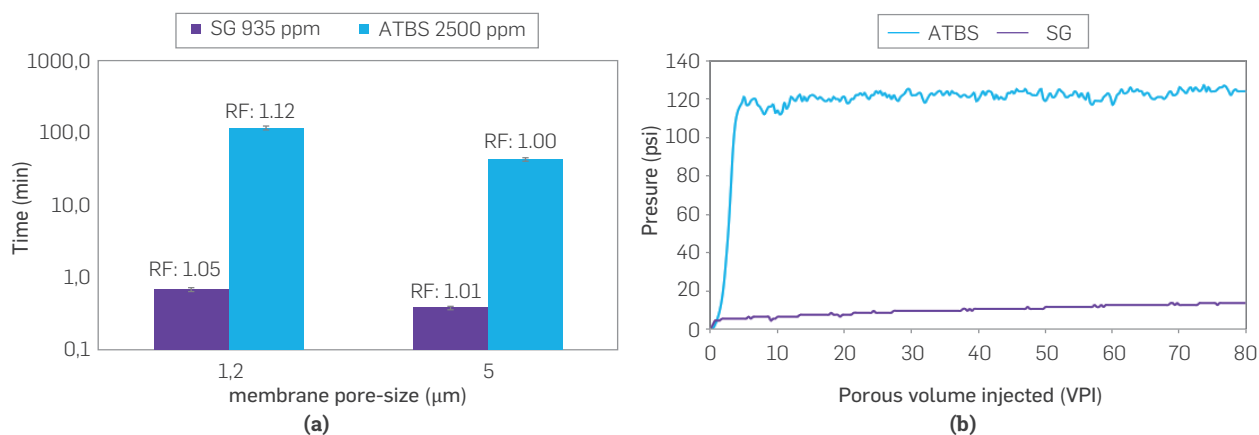


Figure 11. (a) Filterability ratio in nitrocellulose membranes of 1.2 μm and 5 μm pore-sizes, and b) Cumulative filterability ratio in 5 μm filter at a constant flow rate (2 mL/min) of SG (935 ppm) and ATBS (2,500 ppm) polymer solutions in synthetic brine (TDS 3,800 ppm).

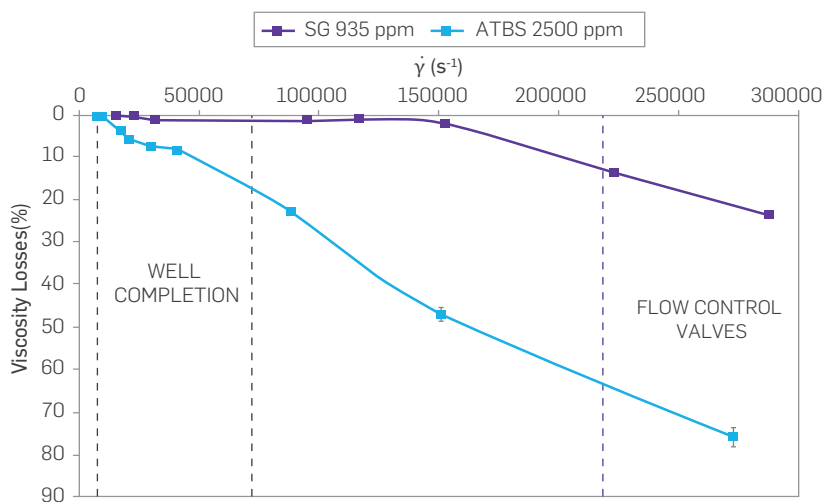


Figure 12. Mechanical stability of SG (935 ppm) and ATBS polymer (2,500 ppm) in synthetic brine (TDS 3,800 ppm) at atmospheric conditions.

CONCLUSIONS

This study compares the performance of Scleroglucan (SG) biopolymer and a commercial sulfonated (ATBS) polymer under different conditions. Overall, SG stands out for generating higher viscosities at lower polymer concentrations and exhibits excellent stability at HTS and high shear rate conditions than the ATBS polymer evaluated.

The shear-thinning flow behavior of Scleroglucan suggests that it should have good injectivity based on the filter ratio results, even with the rod-type structure. The properties exhibited of this

biopolymer make it possible to broaden the range of application restricted oil reservoirs with extreme temperature, salinity, and hardness conditions.

Scleroglucan shows promising properties for EOR applications, including heavy oil reservoirs at high temperature, preserving the viscosity and stability at high salinities (0-5 %w/w), ionic strengths (Na^+ , Ca^{2+} , and Mg^{2+}), up to $275,000 \text{ s}^{-1}$, temperatures ($>80 \text{ }^\circ\text{C}$), and wide pH ranges (3-10), tested in this study.

REFERENCES

- [1] A. Al Adasani and B. Bai, "Analysis of EOR projects and updated screening criteria," *Journal of Petroleum Science and Engineering*, vol. 79, pp. 10-24, 2011. <https://doi.org/10.1016/j.petrol.2011.07.005>
- [2] R. A.-M. Al-Mjeni, S. Arora, P. K. Cherukupalli, J. N. M. V. Wunnik, J. Edwards, B. J. Felber, et al., "Has the time come for EOR?," *Oilfield Review*, 2010. 22, 16-35.
- [3] E. J. Manrique, C. P. Thomas, R. Ravikiran, M. Izadi Kamouei, M. Lantz, J. L. Romero, et al., "EOR: current status and opportunities," in *SPE improved oil recovery symposium*, 2010. <https://doi.org/10.2118/130113-MS>
- [4] R.-H. Castro-García, G.-A. Maya-Toro, R. Jiménez-Díaz, H.-I. Quintero-Pérez, V.-M. Díaz-Guardia, K.-M. Colmenares-Vargas, et al., "Polymer flooding to improve volumetric sweep efficiency in waterflooding processes," *CT&F-Ciencia, Tecnología y Futuro*, vol. 6, pp. 71-90, 2016. <https://doi.org/10.29047/01225383.10>
- [5] K. S. Sorbie, *Polymer-improved oil recovery*: Springer Science & Business Media, 2013. <https://www.springer.com/gp/book/9780216926936>
- [6] A. Abidin, T. Puspasari, and W. Nugroho, "Polymers for enhanced oil recovery technology," *Procedia Chemistry*, vol. 4, pp. 11-16, 2012. <https://doi.org/10.1016/j.proche.2012.06.002>
- [7] G.-A. Maya-Toro, R.-H. Castro-García, R. Jiménez-Díaz, and S.-F. Muñoz-Navarro, "Analysis of mixing parameters for polymer gels used for the correction of water injection profiles," *CT&F-Ciencia, Tecnología y Futuro*, vol. 6, pp. 43-68, 2015. <https://doi.org/10.29047/01225383.26>
- [8] R. Seright, "Potential for polymer flooding reservoirs with viscous oils," *SPE Reservoir Evaluation & Engineering*, vol. 13, pp. 730-740, 2010. <https://doi.org/10.2118/129899-PA>
- [9] R. S. Seright, A. Campbell, P. Mozley, and P. Han, "Stability of partially hydrolyzed polyacrylamides at elevated temperatures in the absence of divalent cations," *SPE Journal*, vol. 15, pp. 341-348, 2010. <https://doi.org/10.2118/121460-PA>
- [10] R. S. Seright, J. M. Seheult, and T. Talashek, "Injectivity characteristics of EOR polymers," in *SPE annual technical conference and exhibition*, 2008. <https://doi.org/10.2118/115142-MS>
- [11] E. Manrique, M. Ahmadi, and S. Samani, "Historical and recent observations in polymer floods: an update review," *CT&F-Ciencia, Tecnología y Futuro*, vol. 6, pp. 17-48, 2017. <https://doi.org/10.29047/01225383.72>
- [12] K. Liang, P. Han, Q. Chen, X. Su, and Y. Feng, "Comparative Study on Enhancing Oil Recovery under High Temperature and High Salinity: Polysaccharides Versus Synthetic Polymer," *ACS Omega*, vol. 4, pp. 10620-10628, 2019. <https://doi.org/10.1021/acsomega.9b00717>
- [13] W. Pu, C. Shen, B. Wei, Y. Yang, and Y. Li, "A comprehensive review of polysaccharide biopolymers for enhanced oil recovery (EOR) from flask to field," *Journal of Industrial and Engineering Chemistry*, vol. 61, pp. 1-11, 2018. <https://doi.org/10.1016/j.jiec.2017.12.034>
- [14] E. Sandvik and J. Maerker, "Application of xanthan gum for enhanced oil recovery," in *ACS Symp. Ser*, 1977, pp. 242-264. <https://doi.org/10.1021/bk-1977-0045.ch019>
- [15] M. A. Al-Saleh, A. A. Yussuf, M. A. Jumaa, A. Hammoud, and T. Al-Shammari, "Biopolymer Solution Evaluation Methodology: Thermal and Mechanical Assessment for Enhanced Oil Recovery with High Salinity Brines," *Processes*, vol. 7, p. 339, 2019. <https://doi.org/10.3390/pr7060339>
- [16] B. Leonhardt, B. Ernst, S. Reimann, A. Steigerwald, and F. Lehr, "Field testing the polysaccharide schizophyllan: results of the first year," in *SPE Improved Oil Recovery Symposium*, 2014. <https://doi.org/10.2118/169032-MS>
- [17] D. Prasad, B. Ernst, G. Incera, B. Leonhardt, S. Reimann, E. Mahler, et al., "Field Testing the Polysaccharide Schizophyllan-Single Well Test Design and Current Results," in *IOR 2017-19th European Symposium on Improved Oil Recovery*, 2017. <https://doi.org/10.3997/2214-4609.201700238>
- [18] B. Kalpakci, Y. Jeans, N. Magri, and J. Padolewski, "Thermal stability of scleroglucan at realistic reservoir conditions," in *SPE/DOE Enhanced Oil Recovery Symposium*, 1990. <https://doi.org/10.2118/20237-MS>
- [19] T. Jensen, M. Kadhum, B. Kozłowicz, E. Sumner, J. Malsam, F. Muhammed, et al., "Chemical EOR Under Harsh Conditions: Scleroglucan As A Viable Commercial Solution," in *SPE Improved Oil Recovery Conference*, 2018. <https://doi.org/10.2118/190216-MS>
- [20] B. Kozłowicz, F. Muhammed, M. Kadhum, M. Khambete, T. Jensen, E. Sumner, et al., "Qualification and Field Injection of Scleroglucan," in *IOR 2019-20th European Symposium on Improved Oil Recovery*, 2019. <https://doi.org/10.3997/2214-4609.201900161>
- [21] M. H. Akstinat, "Polymers for enhanced oil recovery in reservoirs of extremely high salinities and high temperatures," in *SPE Oilfield and Geothermal Chemistry Symposium*, 1980. <https://doi.org/10.2118/8979-MS>
- [22] R. Riveng, A. Donche, and C. Nolk, "Improved scleroglucan for polymer flooding under harsh reservoir conditions," *SPE reservoir engineering*, vol. 7, pp. 15-20, 1992. <https://doi.org/10.2118/19635-PA>
- [23] P. Davison and E. Mentzer, "Polymer flooding in North Sea reservoirs," *Society of Petroleum Engineers Journal*, vol. 22, pp. 353-362, 1982. <https://doi.org/10.2118/9300-PA>
- [24] API, *Recommended Practices for Evaluation of Polymers Used in Enhanced Oil Recovery Operations*. American Petroleum Institute - API Recommended Practice (RP 63). First Edition, June 1, 1990. 86 p.
- [25] R. S. Seright, K. E. Wavrik, G. Zhang, and A. M. AlSofi, "Stability and Behavior in Carbonate Cores for New Enhanced-Oil-Recovery Polymers at Elevated Temperatures in Hard Saline Brines," *SPE Reservoir Evaluation & Engineering*, 2020. <https://doi.org/10.2118/200324-MS>
- [26] P. J. Carreau, "Rheological equations from molecular network theories," *Transactions of the Society of Rheology*, vol. 16, pp. 99-127, 1972. <https://doi.org/10.1122/1.549276>
- [27] K. Yasuda, "Investigation of the analogies between viscometric and linear viscoelastic properties of polystyrene fluids," Thesis (Ph.D.)--Massachusetts Institute of Technology, Dept. of Chemical Engineering, 1979. <http://hdl.handle.net/1721.1/16043>
- [28] M. Vincendon, "Scleroglucan derivatives: Aromatic carbamates," *Journal of Polymer Science Part A: Polymer Chemistry*, vol. 37, pp. 3187-3192, 1999. [https://doi.org/10.1002/\(SICI\)1099-0518\(19990815\)37:16<3187::AID-POLA16>3.0.CO;2-J](https://doi.org/10.1002/(SICI)1099-0518(19990815)37:16<3187::AID-POLA16>3.0.CO;2-J)
- [29] S. Arora, S. Lal, S. Kumar, M. Kumar, and M. Kumar, "Comparative degradation kinetic studies of three biopolymers: chitin, chitosan and cellulose," *Archives of Applied Science Research*, 2011. 3 (3):188-201.
- [30] R. Mansa, L. Dzene, A. Quintela, F. Rocha, and C. Detellier, "Preparation and characterization of novel clay/scleroglucan nanocomposites," *Applied Clay Science*, vol. 126, pp. 235-244, 2016. <https://doi.org/10.1016/j.clay.2016.03.021>
- [31] A. Sabhapondit, A. Borthakur, and I. Haque, "Characterization of acrylamide polymers for enhanced oil recovery," *Journal of Applied Polymer Science*, vol. 87, pp. 1869-1878, 2003. <https://doi.org/10.1002/app.11491>
- [32] D. Biswal and R. Singh, "Characterisation of carboxymethyl cellulose and polyacrylamide graft copolymer," *Carbohydrate polymers*, vol. 57, pp. 379-387, 2004. <https://doi.org/10.1016/j.carbpol.2004.04.020>
- [33] R. P. Chhabra, "Non-Newtonian fluids: an introduction," in *Rheology of complex fluids*, ed: Springer, 2010, pp. 3-34. https://doi.org/10.1007/978-1-4419-6494-6_1

- [34] H. A. Barnes, "A handbook of elementary rheology. Institute of Non-Newtonian Fluid Mechanics," University of Wales, Institute of Non-Newtonian Fluid Mechanics, 2000.
- [35] A. Samanta, A. Bera, K. Ojha, and A. Mandal, "Effects of alkali, salts, and surfactant on rheological behavior of partially hydrolyzed polyacrylamide solutions," *Journal of Chemical & Engineering Data*, vol. 55, pp. 4315-4322, 2010. <https://doi.org/10.1021/jc100458a>
- [36] B. Silveira, L. Lopes, and R. Moreno, "Rheological approach of HPAM solutions under harsh conditions for EOR applications," *International Journal of Engineering & Technology*, IJET-IJENS Vol.16 No:03, 2016.
- [37] S. Antignard, B. Giovannetti, T. Divers, G. Dupuis, N. Gaillard, and C. Favero, "Thermal Stability Evaluation of EOR Polymer: Best Practices & Guidelines," in *IOR 2019-20th European Symposium on Improved Oil Recovery*, 2019. <https://doi.org/10.3997/2214-4609.201900160>
- [38] J. Farina, F. Sineriz, O. Molina, and N. Perotti, "Isolation and physicochemical characterization of soluble scleroglucan from *Sclerotium rofsii*. Rheological properties, molecular weight and conformational characteristics," *Carbohydrate Polymers*, vol. 44, pp. 41-50, 2001. [https://doi.org/10.1016/S0144-8617\(00\)00189-2](https://doi.org/10.1016/S0144-8617(00)00189-2)
- [39] S. C. Viñarta, O. D. Delgado, L. I. Figueroa, and J. I. Fariña, "Effects of thermal, alkaline and ultrasonic treatments on scleroglucan stability and flow behavior," *Carbohydrate polymers*, vol. 94, pp. 496-504, 2013. <https://doi.org/10.1016/j.carbpol.2013.01.063>
- [40] B. Kozłowicz, T. Jensen, M. Khambete, M. J. Kadhum, F. K. Garshot, E. A. Vik, et al., "Scleroglucan Polymer Stability: Thermal, Chemical, and Microbial," in *SPE Improved Oil Recovery Conference*, 2020. <https://doi.org/10.2118/200335-MS>
- [41] M. de Melo and E. Lucas, "Characterization and selection of polymers for future research on enhanced oil recovery," *Chemistry & Chemical Technology*, Vol. 2, 2008.
- [42] J. G. Joosten, J. L. McCarthy, and P. N. Pusey, "Dynamic and static light scattering by aqueous polyacrylamide gels," *Macromolecules*, vol. 24, pp. 6690-6699, 1991. <https://doi.org/10.1021/ma00025a021>
- [43] M. Sletmoen, E. Geissler, and B. T. Stokke, "Determination of molecular parameters of linear and circular scleroglucan coexisting in ternary mixtures using light scattering," *Biomacromolecules*, vol. 7, pp. 858-865, 2006. <https://doi.org/10.1021/bm050990m>
- [44] F. A. T. Hernandez, J. C. L. Niño, and R. L. Moreno, "Effects of salts and temperature on rheological and viscoelastic behavior of low molecular weight HPAM solutions," *Revista Fuentes*, vol. 16, pp. 19-35, 2018. <https://doi.org/10.18273/revfue.v16n1-2018002>
- [45] C. Cooper, P. Dubin, A. Kayitmazer, and S. Turksen, "Polyelectrolyte-protein complexes," *Current opinion in colloid & interface science*, vol. 10, pp. 52-78, 2005. <https://doi.org/10.1016/j.cocis.2005.05.007>
- [46] T. L. Bluhm, Y. Deslandes, R. H. Marchessault, S. Pérez, and M. Rinaudo, "Solid-state and solution conformation of scleroglucan," *Carbohydrate Research*, vol. 100, pp. 117-130, 1982. [https://doi.org/10.1016/S0008-6215\(00\)81030-7](https://doi.org/10.1016/S0008-6215(00)81030-7)
- [47] J. Joanny, L. Leibler, and P. De Gennes, "Effects of polymer solutions on colloid stability," *Journal of Polymer Science: Polymer Physics Edition*, vol. 17, pp. 1073-1084, 1979. <https://doi.org/10.1002/pol.1979.180170615>
- [48] H. J. Berendsen, "Specific interactions of water with biopolymers," in *Water in Disperse Systems*, ed: Springer, 1975, pp. 293-330. https://doi.org/10.1007/978-1-4757-6961-6_6
- [49] A. Palleschi, G. Bocchinfuso, T. Coviello, and F. Alhaique, "Molecular dynamics investigations of the polysaccharide scleroglucan: first study on the triple helix structure," *Carbohydrate research*, vol. 340, pp. 2154-2162, 2005. <https://doi.org/10.1016/j.carres.2005.06.026>
- [50] X. Xin, G. Xu, H. Gong, Y. Bai, and Y. Tan, "Interaction between sodium oleate and partially hydrolyzed polyacrylamide: A rheological study," *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, vol. 326, pp. 1-9, 2008. <https://doi.org/10.1016/j.colsurfa.2008.05.009>
- [51] P. Pincus, "Excluded volume effects and stretched polymer chains," *Macromolecules*, vol. 9, pp. 386-388, 1976. <https://doi.org/10.1021/ma60051a002>
- [52] O. G. Jones and D. J. McClements, "Functional biopolymer particles: design, fabrication, and applications," *Comprehensive Reviews in Food Science and Food Safety*, vol. 9, pp. 374-397, 2010. <https://doi.org/10.1111/j.1541-4337.2010.00118.x>

AUTHORS

Rubén Hernán Castro García

Affiliation:
Ecopetrol S.A., Santander, Colombia
ORCID: <https://orcid.org/0000-0001-7267-4221>
e-mail: rubenHe.castro@ecopetrol.com.co

Sebastián Llanos Gallo

Affiliation:
Universidad Industrial de Santander, Santander, Colombia
ORCID: <https://orcid.org/0000-0002-4774-7043>
e-mail: sllanosg@uis.edu.co

Jenny Liseth Rodríguez Ardila

Affiliation:
Universidad Industrial de Santander, Santander, Colombia
e-mail: jennyira@uis.edu.co

Henderson Iván Quintero Pérez

Affiliation:
Ecopetrol S.A., Santander, Colombia
ORCID: <https://orcid.org/0000-0002-4177-442X>
e-mail: henderson.quintero@ecopetrol.com.co

Jose Francisco Zapata Arango

Affiliation:
Ecopetrol S.A., Bogotá, Colombia
e-mail: Jose.Zapata@ecopetrol.com.co

Eduardo José Manrique Ventura

Affiliation: Ecopetrol S.A., Santander, Colombia
ORCID: <https://orcid.org/0000-0002-0238-8091>
e-mail: eduardo.manrique@ecopetrol.com.co

NOMENCLATURE

<i>HTHS</i>	High-temperature high salinity
<i>SG</i>	Scleroglucan
<i>ATBS</i>	Sulfonated polyacrylamide or 2-acrylamido-tertbutylsulfonic acid)
D_H	Mean hydrodynamic size
λ	Relaxation time index
μ_∞	Fluid behavior at zero stress (cP)
μ_0	Fluid behavior at infinite stress (cP)
n	Pseudoplasticity index
$\dot{\gamma}$	Shear rate (s^{-1})
<i>TDS</i>	Total Dissolved Solids (ppm)
<i>TSS</i>	Total Suspended Solids (ppm)



Profitable recovery

- In the past ten years, the **ICP** has supported the successful implementation **+ 30 treatments with polymeric gels and 9 chemical recovery pilots.**

Impact

Increase between 3% and 4% of the recovery factor in active pilots in the Chichimene, La Cira Infantas, Casabe and Yariguí fields.

Recobro rentable

- En los últimos diez años el **ICP** ha apoyado la implementación exitosa de **+ 30 tratamientos con geles poliméricos y 9 pilotos de recobro químico.**

Impacto

Incremento entre 3% y 4% del factor de recobro en pilotos activos de los campos Chichimene, La Cira Infantas, Casabe y Yariguí.