
ARTICLE INFO

Received : April 24, 2023

Revised : October 30, 2023

Accepted : November 1, 2023

CT&F - Ciencia, Tecnología y Futuro Vol 13, Num 1 June 2023, pages 75-85

DOI: <https://doi.org/10.29047/01225383.668>

STUDY OF FATIGUE CHARACTERISTICS OF KEY WELDS OF MODULAR DRILLING DERRICKS

■ ESTUDIO DE LAS CARACTERÍSTICAS DE FATIGA DE LAS SOLDADURAS CLAVE DE LA TORRE DE PERFORACIÓN DEL MÓDULO

Jialin Tian¹, Zhe Zhang^a, Chenghang Liu^a, Changqing Xiong^a

ABSTRACT

Driven by the gradual development of oil and natural gas resources, the global use of rigs and the number of wells rise steadily. Modular rigs play an important role in oil exploration because of their efficient transport, economy, technological advancement, and rig reliability. The derrick is a key part of the modular rig, and since many essential components in the derrick are welded, the fatigue life of the derrick weld is particularly relevant. In this paper, the modular rig is the object of the research, proposing the calculation formula of fatigue life of the key weld of the derrick. Using modular rig ZJ90D as an example, and combining the rig working conditions with the structural characteristics of the derrick, the key calculation parameters are obtained by numerical analysis. Thus, the life expectancy of the key weld is calculated according to the calculation formula of fatigue life presented herein. The research results have important reference significance and guiding value for the design and optimization of modular rig derricks.

RESUMEN

Impulsado por el desarrollo gradual de los recursos de petróleo y gas natural, el uso global de las plataformas y el número de pozos aumentan constantemente. La plataforma de módulos juega un papel importante en la exploración de petróleo debido a su eficiente transporte, economía, avance tecnológico y confiabilidad de la plataforma. El Derrick es una parte importante de la plataforma del módulo, y dado que muchos componentes importantes en el Derrick están soldados, la vida de fatiga de la soldadura Derrick es particularmente importante. En este trabajo se toma como objeto de investigación el módulo aparejo y se propone la fórmula de cálculo de la vida a fatiga de la soldadura clave de la torre de perforación. Tomando el módulo rig ZJ90D como ejemplo, combinado las condiciones de trabajo de la plataforma del módulo con las características estructurales de la torre de perforación, los parámetros clave de cálculo se obtienen por análisis numérico. Por lo tanto, la esperanza de vida de la soldadura clave se calcula de acuerdo con la fórmula de cálculo de la vida a la fatiga que se presenta en este artículo. Los resultados de la investigación tienen un importante significado de referencia y valor guía para el diseño y optimización de la plataforma de módulo Derrick

KEYWORDS / PALABRAS CLAVE

Module Rig | Derrick | Weld | Numerical Analysis | Fatigue Life
Plataforma de módulos | Derrick | Soldadura | Análisis numérico |
Vida de la fatiga

AFFILIATION

^a Oil and gas equipment technology Sharing and Service Platform of Sichuan Province, School of Mechanical Engineering, Southwest Petroleum University, Chengdu, Sichuan, China
email: 1241709265@qq.com

1. INTRODUCTION

The demand for oil and gas resources is rising, and the world's major oil companies are accelerating the production of energy. The potential of the drilling market is also expanding, and the global rig usage, drilling quantity, and other indicators continue to rise (Wang J. & Wang W., 2011); (Jiarong & Lingjie, 2014). To reduce drilling costs and ancillary costs (transportation and shutdown costs, etc.), the modular rig, as a new rig technology, plays an important role in oil exploration because of its efficient transport, economy, advanced technology, and reliability (Cao L. et al., 2017; Sun Y et al., 2018; Huang Z. et al., 2018).

The derrick is an important piece of the modular rig. It belongs to the large steel frame structure, with numerous rods and complicated forces. It provides support and protection for the entire rig system during the drilling process. Once the structure is damaged, the consequences are unimaginable (Yuanqing., W. 2000; Zu., W., 2017).

Many essential components in the derrick are welded, and the welds at critical locations vary with the conditions of use. Because of the complicated force of the weld at the critical position, in the design and calculation of the weld, not only the operability of the weld at the critical position should be considered, but also the fatigue characteristic of the key weld under different stress conditions (Wang J P & Bao Z F, 2012; Hu J et al., 2013; (Dongying et al., 2011; Chen et al., 2013). Currently, the structural design of a modular rig and the development of supporting control systems and transport devices have achieved certain results (Hua et al., 2016; Ren Deyong et al., 2017). However, there is very little research on the weld of the modular rig derrick. This paper is focused on the modular rig as the research core to analyze the fatigue characteristics of the key weld of the derrick to obtain the necessary scientific basis for the design, manufacture, and safe use of the modular rig.

1. THEORETICAL FRAMEWORK

The allowable stress amplitude method is a fatigue calculation method developed along with a welded steel structure. Through numerous experimental research and engineering practice, it has been proved that welding defects are often the source of fatigue cracks and fatigue damage. Most of the derricks are welded structures, and their fatigue strength is calculated by means of the equation 1,

$$\Delta\sigma \leq \left(\frac{c}{N}\right)^{\frac{1}{M}} \quad (1)$$

Where $\Delta\sigma$ is calculated stress amplitude, c , and M are coefficients, N is the number of stress cycles.

The load on the derrick and the base are unstable, and the fatigue is variable. Therefore, according to the principle of accumulated damage fatigue, it is necessary to convert the variable amplitude fatigue into equivalent normal amplitude fatigue. Equation 1 further evolves into equation 2,

$$\Delta\sigma_c \leq \left(\frac{c}{N}\right)^{\frac{1}{M}} \quad (2)$$

Where $\Delta\sigma_c$ is equivalent stress amplitude, it is defined by equation 3,

$$\Delta\sigma_c = k_c (\sigma_{max} - \sigma_{min}) \quad (3)$$

Where k_c is the equivalent stress amplitude coefficient, σ_{max} is the maximum tensile stress in each stress cycle of weld stress; σ_{max} - weld stress maximum tensile stress in each stress cycle; The load in this working condition is: maximum drill string weight, second floor platform weight, crane weight, second floor derrick and accessories weight, derrick to bear wind load. σ_{min} is the minimum tensile stress or compressive stress in each stress cycle of the weld stress. σ_{min} - weld stress minimum tensile or compressive stress in each stress cycle; (Tensile stress is positive, compressive stress is negative); the load in this working condition is: full vertical root, no hook load, weight of the second floor, weight of the derrick and accessories, and wind load of the derrick.

Although the fatigue strength is calculated by the allowable stress amplitude method, including the effect of the local yield zone due to local stress concentration, the design of the entire component is still made according to the elastic criteria. Since the probability density of the load is continuously changed due to the drilling operation, the equivalent stress amplitude coefficient can be expressed as equation 4.

$$k_c = \left[\frac{fCS}{N_0} \int_0^1 \left(\frac{\alpha_i}{\alpha_{max}}\right)^M \phi d\alpha \right]^{\frac{1}{M}} \quad (4)$$

Where f is the impact coefficient of the drill, C is the number of stress cycles of the derrick when the drill string is raised by 1 m, ϕ is the probability density function of the drilling load, N_0 is the stress cycle base, S is the total number of meters of the rig lifting the drill string during the life of the derrick weld, α is relative drill string weight, for derrick fatigue calculation, $\alpha_{max}=1$.

From the perspective of fatigue calculation, the duration of the drill-down operation is the longest, and the resulting number of stress cycles is the highest. The down-drilling load spectrum is related to the type of drilling rig, well depth, geological conditions, etc., and its load changes from small to maximum, and the frequency of repeated action of the load is equivalent to the ratio of the number of times of drilling down and the depth of the well. Considering the influence of some accidental loads, the probability density function of the tripping load can be expressed by equation 5.

$$\varphi = \frac{1.3}{1+4\alpha^6} \quad (5)$$

And Combine equation 6

$$S = T \cdot z \cdot L \cdot x \quad (6)$$

Deriving the formula for calculating the fatigue life of the derrick weld:

$$T \leq \frac{N_0 \cdot c}{N \cdot f \cdot C \cdot \int_0^1 \frac{\alpha^M}{1+4\alpha^6} d\alpha \cdot (\sigma_{max} - \sigma_{min})^M \cdot z \cdot L \cdot x} \quad (7)$$

Where T is the derrick weld fatigue life, L is the depth of drilling, Z is the average number of drills per well, X is the number of wells in a year.

3. EXPERIMENTAL DEVELOPMENT

From the above theoretical derivation, it can be observed that some parameters are related to the structural properties of the derrick, which can be obtained by consulting the relevant manual. However, some parameters are closely related to the load on the derrick, and it must be calculated based on the analysis of the load condition, such as σ_{max} and σ_{min} . The loads on the derrick mainly include three types: wind load, working load, and dead load.

1. WIND LOAD

Wind load is a random load that changes not only with time but also with spatial position. Depending on the derrick structure, this paper divides the wind load into the wind load on the derrick, and the standpipe.

(1) Wind load on the derrick

The wind load calculation is based on the specifications of API Spec 4F ("API Specification 4F", 2013) version 4, and the wind load calculation formula is

$$F_m = 0.00338 \cdot K_i \cdot V_H^2 \cdot C_s \cdot A \tag{8}$$

$$V_H = V_{des} \cdot \beta \tag{9}$$

Where F_m is the wind perpendicular to the longitudinal axis of the individual component, or the surface of the windshield, or the projected area of the attachment, K_i is the coefficient of the inclination angle between the longitudinal axis of the individual members and the wind, V_H is the local wind speed at height, C_s is shape coefficient, A is the projected area of a single component, β is height coefficient; V_{des} is the maximum rated design wind speed.

(2) Wind load on the standpipe

The schematic diagram of the discharge of standpipe in monkey-board is shown in Fig. 1. Where +X, +Y, -X, -Y represent different wind directions, i and j represent the number of row and column, respectively

$$A_s = m \cdot d \cdot l \cdot \sin\theta \tag{10}$$

Where m is the number of towers on the monkey-board, as the wind comes from the +X or -X direction, $m=i$, as the wind comes from the +Y or -Y direction, $m=j$. d is the outer diameter of the root joint.

2. Working load

The working load is the load generated during the work of the derrick, including the maximum hook load, rated hook load, additional work and handling accident hook load, the force of working line, standpipe load, and so on. The working load to be considered in the derrick static calculation mainly includes the maximum hook load, the rated hook load, the force of the working line, and the standpipe load.

(1) Maximum hook load

The maximum hook load is the maximum lifting weight of the hook when the dead rope is fixed at the designated position, the number of drilled ropes is specified, and there is no wind load, and the second

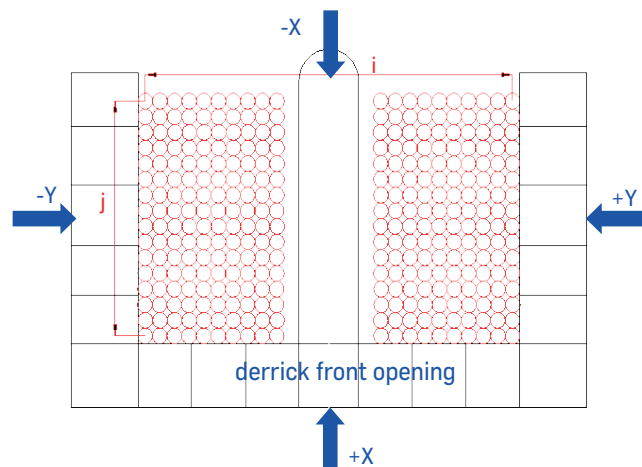


Figure 1. Schematic diagram of the discharge of standpipe in monkey-board and the direction of the wind

floor does not store either the stand or the sucker rod. It does not include the weight of the crown block, traveling block, and the hook. (2) Rated hook load

The rated hook load is also called the maximum drill string weight. When drilling to the maximum well depth, the rated load is the weight of all drill strings suspended from the hook. Generally, it can be derived from

$$Q_R = q \cdot L \tag{11}$$

Where Q_R is the rated hook load, q is the average weight per meter of the drill string, L , the weight per unit length.

(3) Force of the working line

The force of the working line is the resultant force of the hook load on the fast rope and the dead rope under a given traveling system. The action point acts on the crown block, and the general direction of the force does not follow the direction of the center of the crown block. The horizontal component is generally small and negligible, and its vertical component can be approximated as:

$$Z \cdot P_i = 2(Q_{max} + G_s) \tag{12}$$

Where P_i is the force of the working line, Q_{max} is the maximum design hook load of derrick, G_s is the weight of the traveling system, Z is the effective number of working line in the traveling system.

(4) Standpipe load

The standing load is composed of the horizontal and vertical component forces caused by the vertical weight of the stand on the drill floor during the drilling process. The horizontal component force acts on the fingerboard of monkey-board, pointing to the two sides of the monkey-board, and the vertical component force acts directly on the rig base in the vertical direction.

The horizontal force of the standpipe can be calculated by the following formula:

$$P_L = \frac{1}{2} q \cdot l \cdot n \cdot \cot\theta \tag{13}$$

Where P_L is the horizontal force of standpipe on the derrick, θ is the angle between standpipe and the plane of monkey-board, n is the amount of standpipe; l is the length of the standpipe.

3. Dead load

The dead load to be considered in the calculation of the derrick mainly includes the weight of the derrick, the weight of monkey-board, the weight of the crown block, and the weight of the traveling system.

4. RESULTS

Using the module rig ZJ90D as an example, given the structural complexity of the derrick, traditional theoretical calculations are difficult to obtain the key parameters σ_{max} and σ_{min} , so the numerical simulation is preferred. To improve the success rate of meshing and reduce the computational workload, the shape and size of the derrick are simplified according to the specific characteristics (Ren, H. & He., J. 2017), and the simplified derrick model and key weld position are shown in Fig. 2. The derrick is made of 16Mn material. The yield strength of the well frame and the weld is 345MPa and 532.1Mpa (Matti R. at el,2022), respectively, and the elastic modulus of both are 210 GPa, and the Poisson's ratio is 0.3. A Strain Gauge is a sensor used to measure the strain of an object. It is based on the fact that the resistance of conductive or semiconductor materials changes with the degree of strain. The strain gauge is usually implemented by pasting or mounting a conductive or semiconductor material on the surface of the object to be measured. Measuring changes in the strain gauge is usually done via an external circuit. The strain gauge is connected to the bridge circuit, which consists of an excitation power supply, a resistance meter, and a measuring device. During the experimental test, clean the weld surface to ensure that it is free of dust, grease, or other impurities, paste the strain gauge on the weld of the derrick, connect the wire to the bridge, the strain collector (ASMB2-16) and the computer, add the external load in the predetermined way, analyze the data, calculate the strain value, and calculate the corresponding stress value according to the mechanical properties of the material. The experimental test device is shown in Fig. 3.

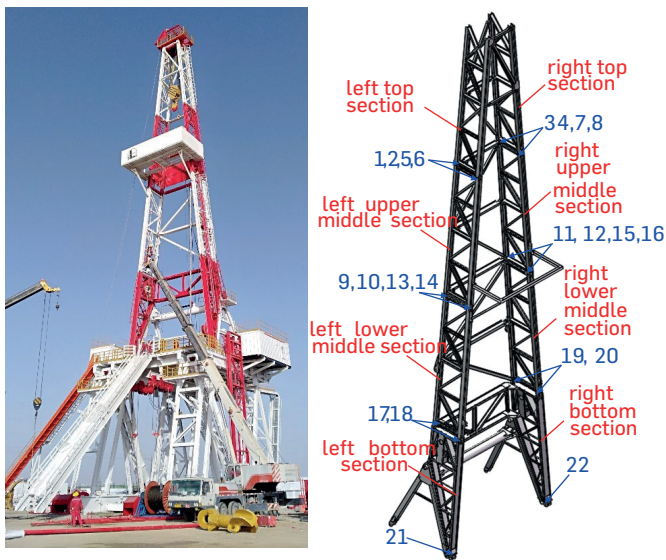


Figure 2. Module rig derrick simplified 3D model and weld position

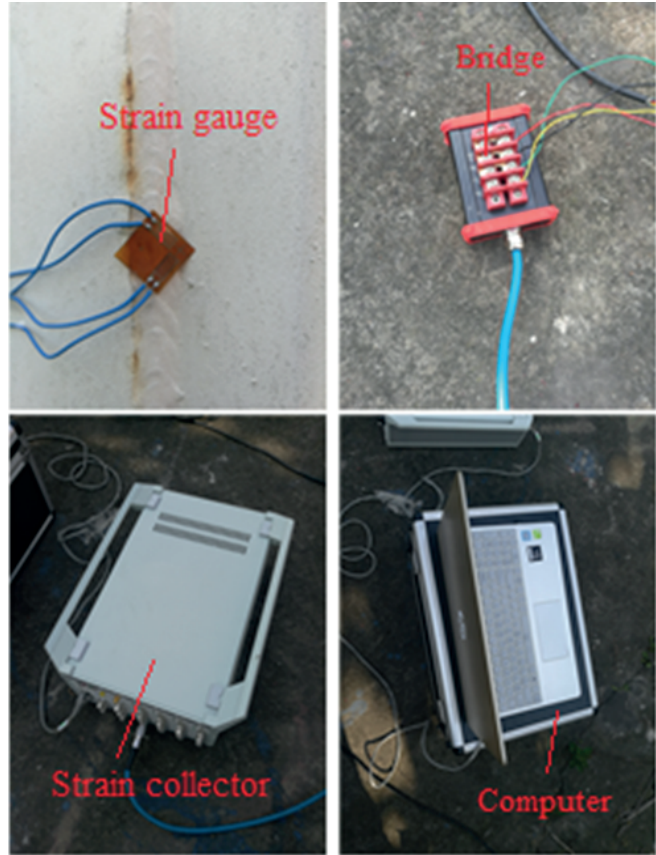


Figure 3. experimental test device

When analyzing the key welds of the derrick and determining the calculated load, it is necessary to fully understand the structural characteristics and technical parameters of the derrick. The main technical parameters of the derrick are shown in table 1. The main parameters are as follows: $c = 4.06 \times 10^{11}$, $N = 5 \times 10^6$, $M = 3$, $C = 1/28$, $N_{00} = 5 \times 10^6$, $L = 9000m$, $ll = 28m$, $q = 36kg/m$, $\theta = 87^\circ$, $d = 0.127m$.

Table 1. Main technical parameters of derrick

Item	Parameter
Maximum hook load (7×8 wheel train, no wind load, no standpipe)	7000kN
Effective height of the derrick	48.8m
Height of the monkey-board	26.5m
Standpipe capacity of the monkey-board (φ127mm drill pipe, 28m standpipe)	9000m
Wind resistance:	
a. Waiting for the weather (no hook, second-floor storages full of standpipe)	36m/s
b. Equipment preservation (no hook load, second floor has no standpipe)	47.8m/s
c. derrick lifting	≤7.8m/s

The calculation results of wind load on the derrick at different wind speeds are shown in table 2. In particular, the -X, -Y wind and the +X, +Y wind load are in the same amount of force, but in opposite direction, respectively.

Table 2. Wind load size of the derrick at different wind speeds (kN)

Position	Wind speed	16.5m/s			36m/s			47.8m/s		
		+X	+Y	+X,+Y	+X	+Y	+X,+Y	+X	+Y	+X,+Y
top section		5.72	5.92	8.24	27.25	28.21	39.22	48.06	49.74	69.16
upper middle section		10.55	7.44	12.73	50.25	34.45	60.60	88.61	62.50	106.85
lower middle sections		8.71	6.21	10.55	41.50	29.57	50.26	73.17	52.15	88.61
bottom section		5.03	4.66	6.86	23.97	22.22	32.66	42.27	39.18	57.59
standpipe		26.02	20.87	33.15	123.86	99.3	157.85	218.38	175.18	278.29

The numerical analysis of the key welds of the derrick includes the following four conditions:


Condition 1: Maximum hook load (7000 KN) + rig structure and attachment weight + standpipe load (4500 KN) + wind load at speed of 16.5m/s + top drive torque.

Condition 2: Maximum turntable load (7000 KN) + rig structure and attachment weight + standpipe load (4500 KN) + wind load at speed of 16.5m/s.

Condition 3: Standpipe load (4500 KN) + maximum turntable load (7000 KN) + rig structure and attachment weight + wind load at speed of 36m/s.

Condition 4: Rig structure and attachment weight + maximum turntable load (7000 KN) + wind load at a speed of 47.8m/s.

In the analysis process, considering the different loads of the derrick during the drilling operation, the drilling process is divided into two

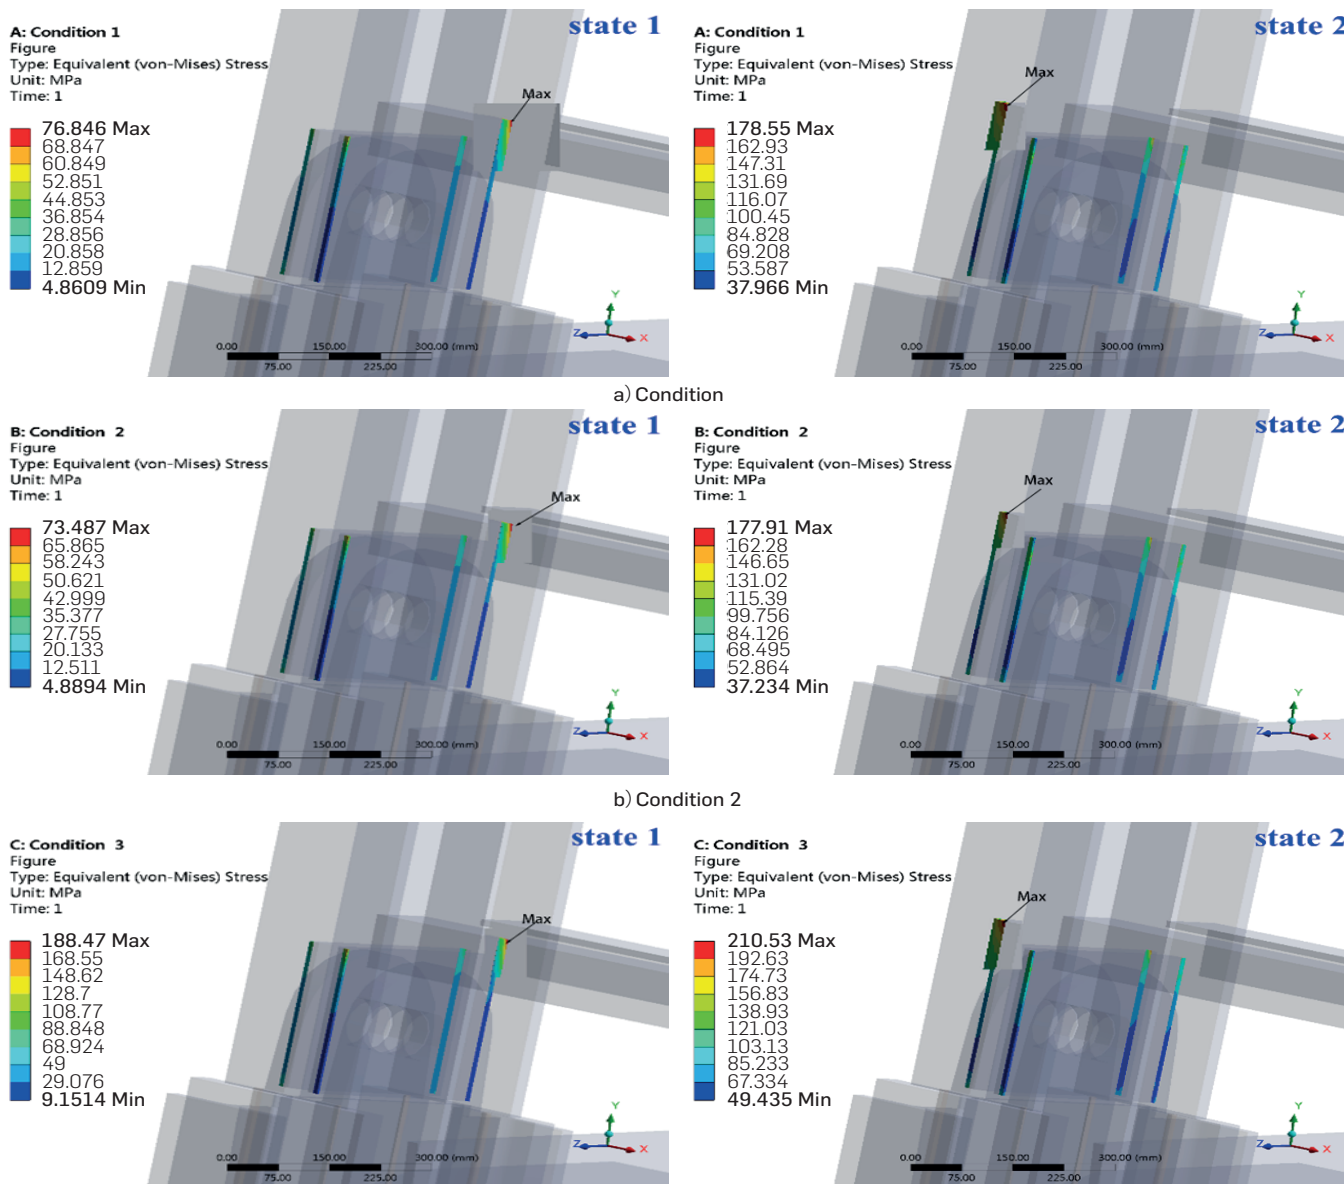

working states. State 1: Rig structure and attachment weight + wind load + (top drive torque) + standpipe load. State 2: Rig structure and attachment weight + wind load + (top drive torque) + drill string weight.

Through the analysis of finite element software, when the wind is coming from +X direction, the stress of the welds in each section of the derrick is the most dangerous. The stress analysis results at position 17 of the lower section of the derrick are shown in Fig. 4.

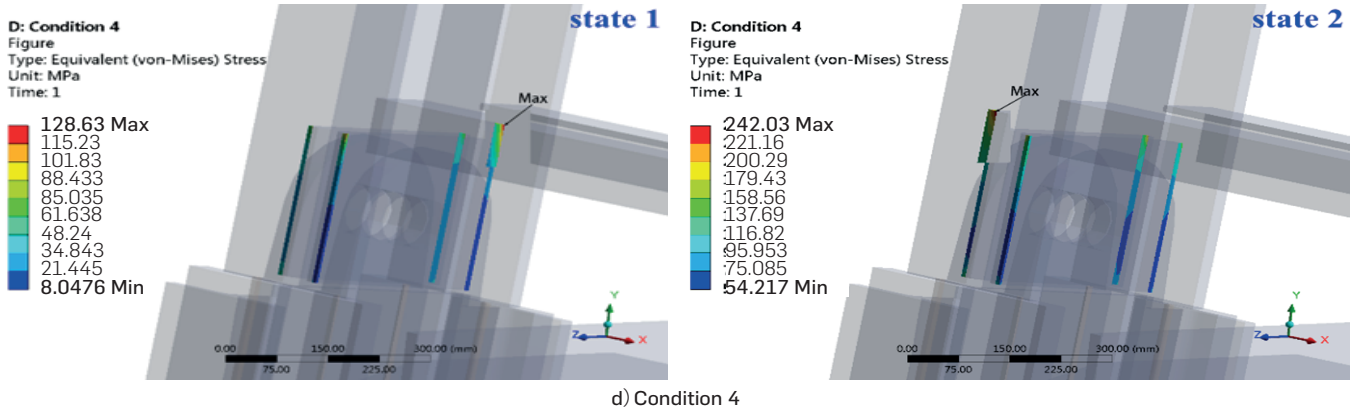


Figure 4. Weld stress results at position point 17 under four conditions in +X direction wind

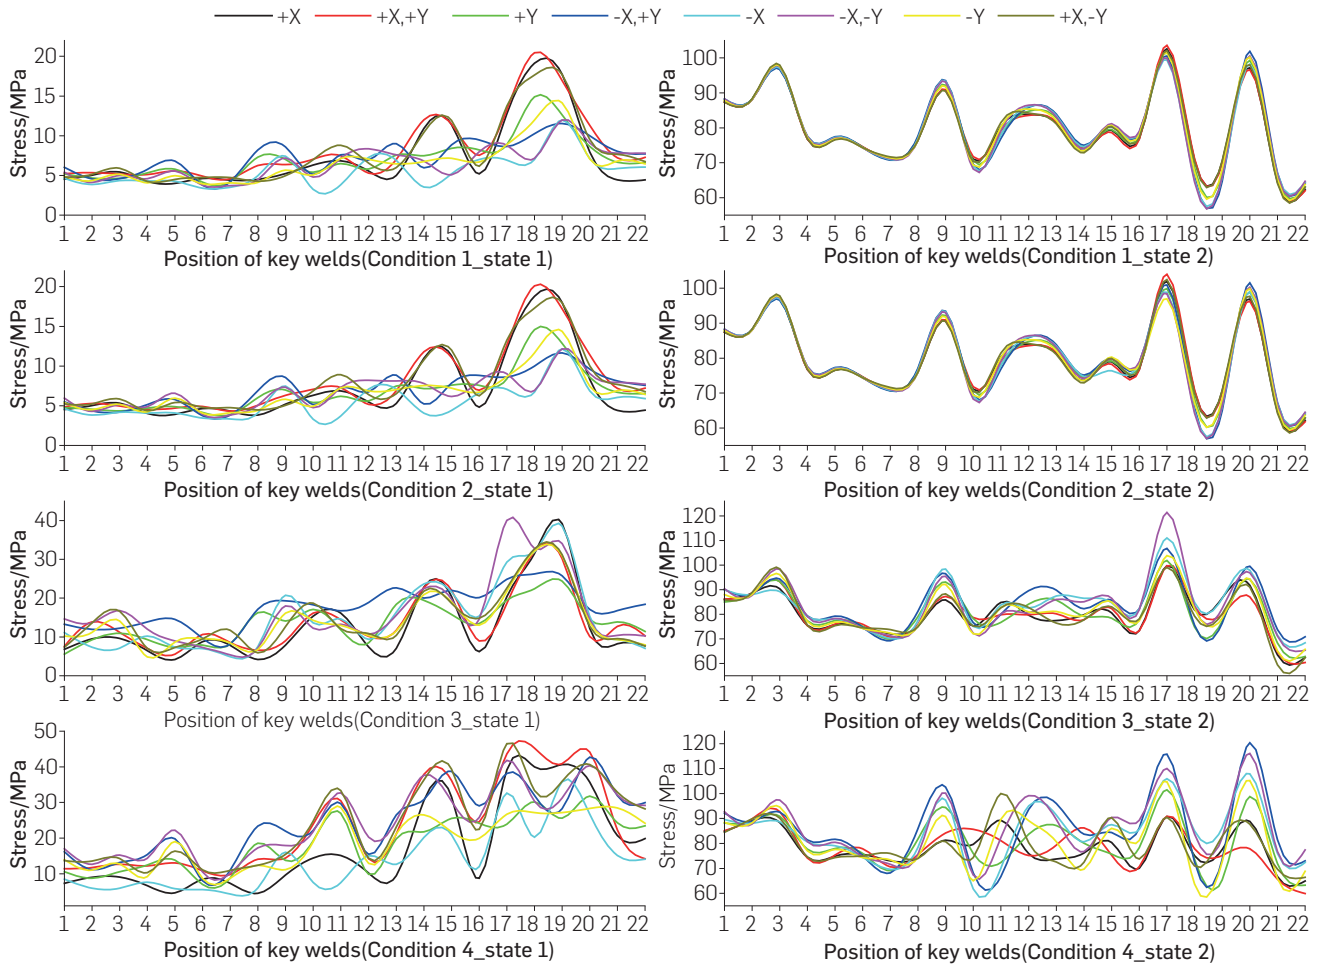


Figure 5. Comparison of different conditions and different wind downward stress results

The stress analysis results of the welds in each section of the derrick are compared and analyzed in four conditions, as shown in Fig. 5. From the results, the stress results are less than the allowable stress of the weld material, within the safe range, meeting the safety requirements. The difference between condition 1 and condition 2 is whether there is a top drive torque. However, it can be noted from the calculation results that the top drive torque has little effect on weld stress. Based on the load combination of condition 2, the wind load of condition 3 continues to increase, and the weld stress of derrick also increases. Condition 4 differs from conditions 1, 2, and 3. There is no standpipe load in the load combination of condition 4, the wind load continues to increase, and the weld stress gradually increases from the top section to the bottom section of the derrick. Analysis of stress results of welds at different positions of the derrick, the weld stress in the middle section of the derrick is relatively close, and the weld stress in the upper and the lower sections of the derrick fluctuates. Moreover, the weld stress in the lower section of the derrick changes substantially, and the greater the stress fluctuation, the more dangerous the rig fatigue failure.

To verify the accuracy of the simulation analysis, the stress value of position 17~20 in condition 1, condition 2 and condition 3 was tested, and the simulated analysis value was compared with the test value, as shown in Fig. 6. The simulation analysis results show the same trend as the test results, and are within error tolerance. Among them, S1, S2, and S3 represent the simulated analysis values in conditions 1, 2, and 3, respectively. T1, T2, and T3 represent the test values in conditions 1, 2, and 3, respectively. As can be observed in Fig. 6, the numerical simulation results are close to the actual test results, so the analysis method is reliable. The numerical simulation

results are slightly different from the actual test results, which is due to the accuracy of the test method and instrument, testing environment, and other factors.

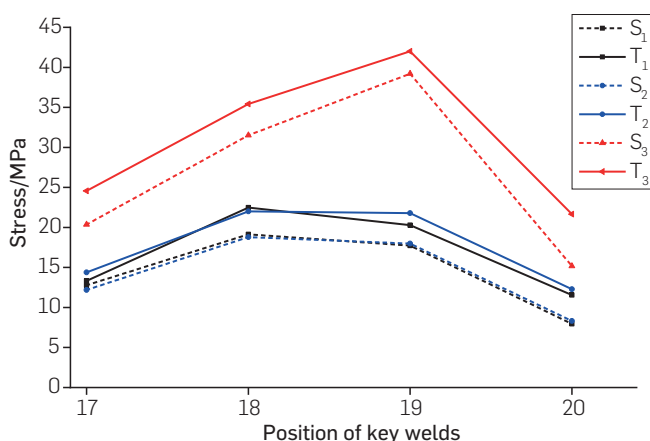


Figure 6. Comparison between simulation analysis and test

5. RESULTS ANALYSIS

1. Theoretical calculation results

(1) Operating condition 1

The results obtained by theoretical calculation under working condition 1 are shown in Table 3. According to the fatigue calculation

Table 3. Fatigue life of key weld of derrick under working condition 1 (years)

weld position	+X	+X,+Y	+Y	-X,+Y	-X	-X,-Y	-Y	+X,-Y
	T	T	T	T	T	T	T	T
1	30	31	31	32	31	30	30	31
2	30	30	29	29	31	32	33	32
3	23	24	22	24	26	25	23	22
4	39	38	37	41	39	37	38	37
5	44	44	43	42	41	42	42	41
6	46	46	47	45	46	45	44	45
7	49	50	49	52	48	51	50	51
8	40	42	41	44	42	42	40	43
9	25	26	25	25	24	23	24	25
10	51	53	54	54	53	52	55	52
11	40	43	42	44	40	41	43	42
12	23	24	24	23	22	24	23	23
13	34	35	24	24	25	25	28	35
14	54	56	42	43	27	32	35	53
15	51	53	39	40	25	31	35	52
16	77	91	89	91	77	80	78	80
17	25	26	23	27	24	24	24	25
18	102	108	97	94	92	93	95	100
19	100	105	93	95	94	97	96	105
20	60	64	49	52	48	54	53	62
21	72	103	103	99	101	102	103	70
22	95	108	98	96	93	106	97	96

Table 4. Fatigue life of key weld of derrick under working condition 2 (years)

weld position	+X	+X,+Y	+Y	-X,+Y	-X	-X,-Y	-Y	+X,-Y
	T	T	T	T	T	T	T	T
1	31	31	31	32	31	30	30	31
2	30	30	29	29	31	32	33	32
3	24	24	22	24	26	25	22	22
4	39	37	37	41	39	37	38	37
5	44	44	43	42	41	42	42	41
6	46	46	47	45	43	45	44	46
7	49	50	49	52	48	51	50	51
8	40	42	41	44	42	42	41	43
9	26	26	25	25	24	23	24	25
10	51	53	54	54	53	52	55	52
11	41	43	41	44	40	41	43	42
12	23	24	24	23	22	24	23	23
13	34	35	24	24	25	25	28	35
14	54	56	42	40	26	32	34	53
15	51	53	39	40	25	31	35	52
16	77	91	89	91	77	80	78	80
17	25	26	22	26	24	24	24	24
18	102	108	97	94	92	93	95	100
19	101	104	94	95	94	96	96	105
20	60	64	48	52	48	54	53	62
21	72	103	103	99	101	102	103	70
22	94	108	98	96	93	106	96	97

Table 5. Fatigue life of key weld of derrick under working condition 3 (years)

weld position	+X	+X,+Y	+Y	-X,+Y	-X	-X,-Y	-Y	+X,-Y
	T	T	T	T	T	T	T	T
1	25	26	24	25	23	27	26	25
2	26	27	25	25	24	27	26	24
3	21	17	18	21	20	19	18	20
4	33	35	34	39	33	34	28	36
5	32	33	34	43	33	32	32	36
6	36	35	33	44	35	34	42	41
7	34	33	32	44	44	30	38	32
8	32	31	27	39	41	25	32	23
9	27	26	26	24	26	27	25	28
10	34	35	34	35	40	33	37	38
11	33	39	35	45	31	34	32	30
12	27	26	26	28	28	29	27	31
13	34	36	25	28	28	23	29	37
14	60	62	35	33	32	31	56	58
15	54	56	46	41	45	28	32	54
16	32	34	27	23	22	35	25	32
17	28	24	27	23	22	25	25	33
18	76	75	67	74	78	84	86	94
19	85	87	63	80	82	81	93	95
20	47	50	36	34	29	31	33	53
21	67	82	77	74	35	39	63	80
22	95	84	81	79	38	35	56	61

Table 6. Fatigue life of key weld of derrick under working condition4 (years)

weld position	+X	+X,+Y	+Y	-X,+Y	-X	-X,-Y	-Y	+X,-Y
	T	T	T	T	T	T	T	T
1	39	36	33	36	33	34	35	41
2	38	36	32	34	32	31	33	40
3	39	36	33	36	33	34	35	41
4	40	37	35	38	35	37	38	45
5	40	42	44	40	45	47	50	53
6	40	41	40	43	42	42	43	45
7	43	42	45	52	40	49	46	45
8	40	42	45	52	38	49	46	46
9	40	41	43	51	36	48	45	43
10	36	40	41	134	43	100	90	78
11	36	80	97	203	48	89	54	68
12	40	71	51	41	30	48	43	65
13	97	56	64	46	37	81	79	126
14	144	146	76	121	50	178	151	234
15	148	197	97	155	40	121	87	159
16	88	165	94	89	38	64	58	125
17	102	146	85	90	37	58	61	145
18	238	328	103	109	52	84	185	204
19	206	312	144	110	85	89	126	132
20	102	301	78	60	40	63	80	115
21	117	164	120	92	53	114	200	226
22	124	116	194	173	60	103	160	217

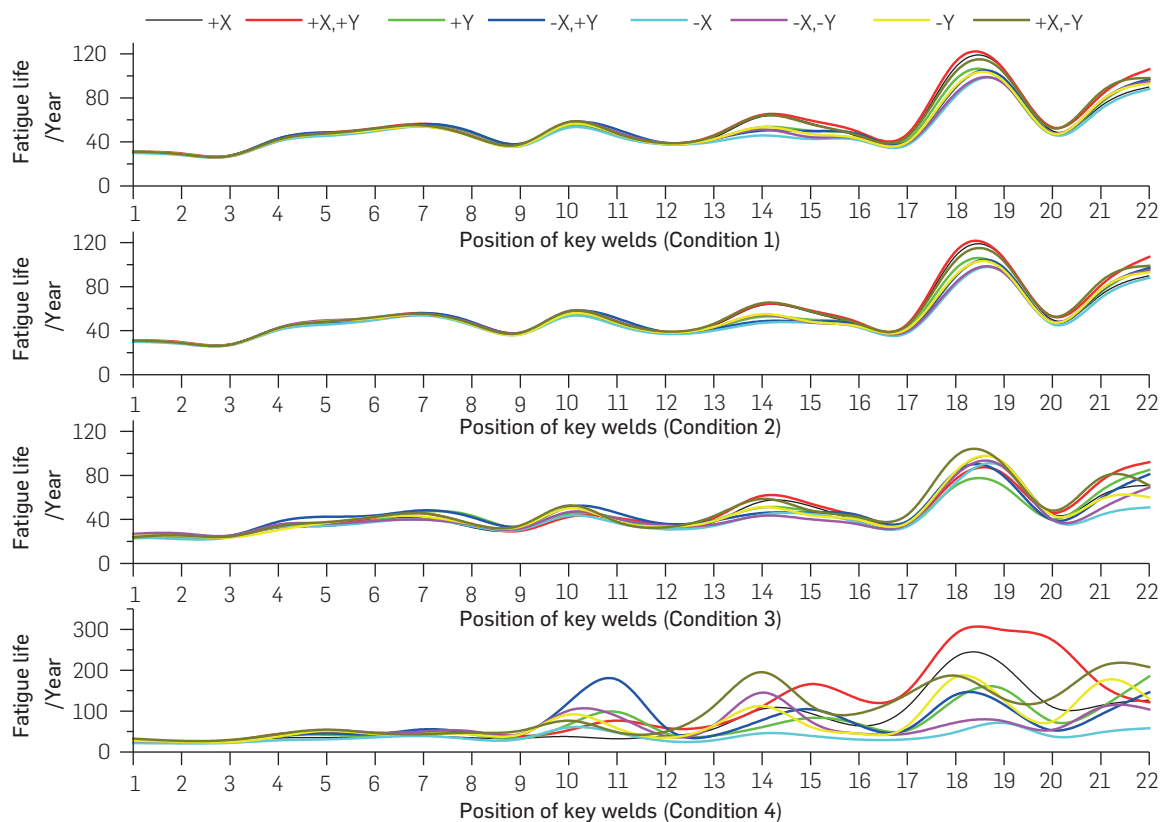


Figure 7. Calculation results of fatigue life under different conditions

results, the fatigue life of most welds is 30–120 years, and the lowest fatigue life is 22 years. The weld life of the upper section of the derrick is roughly between 35 and 120 years.

(2) Operating condition 2

The results under working condition 2 are shown in Table 4. According to the fatigue calculation results, the fatigue life of most welds is 24–120 years, and the lowest fatigue life is 22 years.

3) Operating condition 3

Working condition 3 is based on the combined load of working condition 2, and the wind load increases, so its change shows the same trend. The results are shown in Table 5. With the distribution law of working condition 2, according to the fatigue calculation results, the fatigue life of most welds is 30–120 years, and the lowest fatigue life is 21 years.

(4) Operating condition 4

The calculation results of working condition 4 are shown in Table 6. According to the fatigue calculation results, the fatigue life of most welds is 30–150 years, and the lowest fatigue life is 31 years.

2. Weld fatigue simulation calculation

According to the weld fatigue calculation formula and stress results, the fatigue life of the key weld of the derrick under various conditions is obtained, as shown in Fig. 7.

According to the fatigue calculation results, the fatigue life of the upper and middle welds of the derrick is shorter. Furthermore, the fatigue life of the welds in the lower section of the derrick is quite different; in particular, the fatigue life of weld position 18 and 19 is longer than in other positions, having to do with the magnitude of the stress in that position. Under condition 1, the minimum fatigue

life of key welds is 22 years, and the weld life of other positions in the derrick is roughly between 27 and 120 years. Under condition 2, the minimum fatigue life of key welds is 22 years, and the weld life of other positions at the derrick is about 28–120 years. Condition 3 is based on the combined load of condition 2; the wind load increases, so the change shows the same trend. The minimum fatigue life of the key weld is 21 years, and the weld life of other positions of the derrick is about 23–120 years. Under condition 4, the minimum fatigue life of key welds is 21 years, and the weld life of other positions in the derrick is roughly between 22 and 300 years.

CONCLUSIONS

1. With the modular drilling rig being the object of study, the calculation formula for the fatigue life of the well welded seam was proposed. Then, with the ZJ90D modular rig drill as the analysis case, in combination with the working condition and structure characteristics of well shelf, using limited element software for the analysis, the key calculation parameters were obtained.
2. Based on the analysis, the stress results are lower than the permissible stress of the welding material in the four working conditions, meeting the safety requirements within the safety scope. Through the fatigue life analysis of the key welds of the well shelf, the fatigue life of the upper and middle welds is shorter, and the fatigue life of the lower weld varies greatly. Combined with the limited fatigue analysis and fatigue lifespan calculation, the maximum position of the accumulated fatigue damage of the soldering weld is determined, laying a good foundation for the optimized design of the future modular drill shelf.

ACKNOWLEDGEMENTS

All authors gratefully acknowledge the support of the State Scholarship Fund of the China Scholarship Council (CSC) (No. 201608515039), National Natural Science Foundation of China (NSFC) (No. 51674216), National Science and Technology Major Project (No. 2016ZX05038).

REFERENCES

- Cao, L. T., Xu, S. P., Zhang, Y. H., Umar, Daguti, & Wang, D. (2017). Technical analysis of 7 000 m bi-directional mobile modular drilling rig base. *China Petroleum Machinery*, 2017, 45(04), 7-11. https://caod.oriprobe.com/articles/52862994/Technical_Analysis_of_the_Substructure_of_the_7_00.htm
- Chen, X., Zhou, S., & Hua, J. (2013). Finite Element Static Analysis of Deep-well Rig Derrick and Substructure System. *China Petroleum Machinery*, 2013, 41(07), 19-21. https://caod.oriprobe.com/articles/39026631/shen_jing_zuan_ji_jing_jia_ji_di_zuo_xi_tong_de_yo.htm
- Dongying, H., Peiming, S., Guoqiang, Z., Zifeng, L., Xujia, L., & Lianjin, W. (2011). Safety evaluation of marine derrick steel structures based on dynamic measurement and updated finite element model. *Procedia Engineering*, 26, 1891-1900. <https://doi.org/10.1016/j.proeng.2011.11.2381>.
- Hua, J., Zhu, H. W., Zhou, S. Z., Hu, L., & Cui, H. (2016). Harmonic Response Analysis and Structure Modification for Substructure of Deep Well Drilling Rig. *Applied Mechanics and Materials*, 826, 45-49. <https://doi.org/10.4028/www.scientific.net/AMM.826.45>
- Huang, Zebin, Chen, Tao, Wang, Peng, Xi, Honglei, & Du, Kanfang. (2018). Bow-Tie risk management modeling of top drive system for modular drilling rigs in the eastern South China Sea. *China Petroleum Machinery*, 2018, 46(02), 47-52. <http://html.rhhz.net/syjsxz/html/20180209.htm>
- Jiarong, L., & Lingjie, R. (2014). The development of deep borehole permanent-magnet motor direct drive top-driving drilling rig. *Procedia Engineering*, 73, 143-149. <https://doi.org/10.1016/j.proeng.2014.06.182>
- Jun, H., Yougang, T., & Shixi, L. I. (2013). Vibration test and assessment for an ocean drilling rig derrick: Taking the ZJ50/3150DB drilling rig as an example. *Petroleum Exploration and Development*, 40(1), 126-129. [https://doi.org/10.1016/S1876-3804\(13\)60014-2](https://doi.org/10.1016/S1876-3804(13)60014-2)
- Rautiainen, M., Remes, H., Niemelä, A., & Romanoff, J. (2023). Fatigue strength assessment of complex welded structures with severe force concentrations along a weld seam. *International Journal of Fatigue*, 167, 107321. <https://doi.org/10.1016/j.ijfatigue.2022.107321>.
- Ren, H., & He, J. (2017). The Design, Calculation, Validation of the Mast and Its Weld Joints for the Water Drilling Rig. *Machine Design & Research*, (2017), 33(02), 101-103. https://www.qk.sjtu.edu.cn/mdr/EN/volumn/volumn_2512.shtml
- Ren, D., Pang, S., & WU, P. (2017). Design Calculation of PJP-Groove Welds on Derrick of the Quick-Carrying Drilling Rig. *Mechanical Research & Application*, 2017, 30(01), 90-92, 98. https://caod.oriprobe.com/articles/50696764/Design_Calculation_of_PJP_Groove_Welds_on_Derrick_.htm
- Specification, A. P. I. (2008). Specification for Drilling and Well Servicing Structures. <http://mycommittees.api.org/standards/techinterp/epequip/shared%20documents/4fti.pdf>.
- Sun, Y., Shi, Y., Wang, Q., & Yao, Z. (2018). Study on speed characteristics of hydraulic top drive under fluctuating load. *Journal of Petroleum Science and Engineering*, 167, 277-286. <https://doi.org/10.1016/j.petrol.2018.04.003>.
- Wang, J. P., & Bao, Z. F. (2013). The Stress Analysis of Drilling Derrick Structure Based on Finite Element

Method. *Applied Mechanics and Materials*, 251, 84-90. <https://doi.org/10.4028/www.scientific.net/AMM.251.84>

Wang, Y. Q., Yuan, Y. Z., & Zhou, G. Q. (2001). Double Nonlinear Analysis of The Loading Capacity of Drilling Derrick Steel Structures Containing Defects and Defacements. *Advances in Structural Engineering*, 4(1), 43-49. <https://doi.org/10.1260/1369433011502336>.

Wang, J., Zhao, H., Zou, J., Zhou, H., Wu, Z., & Du, S. (2017). Welding distortion prediction with elastic FE analysis and mitigation practice in fabrication of cantilever beam component of jack-up drilling rig. *Ocean Engineering*, 130, 25-39. <https://doi.org/10.1016/j.oceaneng.2016.11.059>

Wang, J., & Wang, W. (2011). Current status of foreign drilling rig technology and China's development strategy. *Petroleum Machinery*, 39(6), 65-69. <http://www.cqvip.com/qk/94770x/20116/38126300.html>.

Zu Wei. (2017). Research on structural design of modular drilling rig with tension leg platform in Liuhua oilfield. *China Petroleum Machinery*, 2017, 45(01), 58-61. <http://html.rhhz.net/syjzz/html/20170113.htm>

AUTHORS

Jialin Tian

Affiliation: School of Mechanical Engineering, Southwest Petroleum University, Chengdu, Sichuan 610500, China
ORCID: <https://orcid.org/0000-0002-9991-9839>
e-mail: tianjialin001@gmail.com

Zhe Zhang

Affiliation: School of Mechanical Engineering, Southwest Petroleum University, Chengdu, Sichuan 610500, China
ORCID: <https://orcid.org/0009-0004-3436-4803>
e-mail: 1241709265@qq.com

Chenghang Liu

Affiliation: School of Mechanical Engineering, Southwest Petroleum University, Chengdu, Sichuan 610500, China
ORCID: <https://orcid.org/0000-0002-2872-0304>
e-mail: hang1042715288@qq.com

Changqing Xiong

Affiliation: School of Mechanical Engineering, Southwest Petroleum University, Chengdu, Sichuan 610500, China
ORCID: <https://orcid.org/0000-0001-5778-7746>
e-mail: changqing0620@qq.com

How to cite: Tian, J. et al. (2023). Study of fatigue characteristics of key welds of module rig derrick. *CT&F -Ciencia, Tecnología y Futuro*, 13(1),75-85 <https://doi.org/10.29047/01225383.668>

NOMENCLATURE

$\Delta\sigma$	<i>calculated stress amplitude</i>
N	<i>the number of stress cycles</i>
$\Delta\sigma_c$	<i>equivalent stress amplitude</i>
k_c	<i>the equivalent stress amplitude coefficient</i>
σ_{max}	<i>the maximum tensile stress in each stress cycle of weld stress</i>
σ_{min}	<i>the minimum tensile stress or compressive stress in each stress cycle of the weld stress</i>
f	<i>the impact coefficient of the drill</i>
C	<i>the number of stress cycles of the derrick when the drill string is raised by 1 m</i>
ϕ	<i>the probability density function of the drilling load</i>
$N0$	<i>the stress cycle base</i>
S	<i>the total number of meters of the rig lifting the drill string during the life of the derrick weld</i>
α	<i>relative drill string weight</i>
T	<i>the derrick weld fatigue life</i>
L	<i>the depth of drilling</i>
Z	<i>the average number of drills per well</i>
X	<i>the number of wells in a year</i>
Fm	<i>the wind perpendicular to the longitudinal axis of the individual component, or the surface of the windshield, or the projected area of the attachment</i>
K_i	<i>the coefficient of the inclination angle between the longitudinal axis of the individual members and the wind</i>
V_H	<i>the local wind speed at height</i>
C_s	<i>shape coefficient</i>
A	<i>the projected area of a single component</i>
β	<i>height coefficient</i>
V_{des}	<i>the maximum rated design wind speed</i>
i	<i>the number of row</i>
j	<i>the number of column</i>
Q_R	<i>the rated hook load</i>
L	<i>the weight per unit length</i>
P_l	<i>the force of the working line</i>
Q_{max}	<i>the maximum design hook load of derrick</i>
G_s	<i>the weight of the traveling system</i>
Z	<i>the effective number of working line in the traveling system</i>
PL	<i>the horizontal force of standpipe on the derrick</i>
	<i>the angle between standpipe and the plane of monkey-board</i>
n	<i>the amount of standpipe</i>
l	<i>the length of the standpipe</i>